



UNIVERSITY OF HELSINKI

<https://helda.helsinki.fi>

Advancement of membrane separation technology for organic pollutant removal

Kafle, Saroj Raj; Adhikari, Sangeet; Shrestha, Rakesh; Ban, Sagar; Khatiwada, Gaurav ...

2024-05-01

IWA Publishing

<http://hdl.handle.net/10138/575801>

Kafle, S R, Adhikari, S, Shrestha, R, Ban, S, Khatiwada, G, Gaire, P, Tuladhar, N, Jiang, G & Tiwari, A 2024, 'Advancement of membrane separation technology for organic pollutant removal', *Water science and technology : a journal of the International Association on Water Pollution Research*, vol. 89, no. 9, pp. 2290-2310. <https://doi.org/10.2166/wst.2024.117>

Downloaded from Helda, University of Helsinki institutional repository. <https://helda.helsinki.fi>
This is an electronic reprint of the original article.
This reprint may differ from the original in pagination and typographic detail.
Please cite the original version.

Advancement of membrane separation technology for organic pollutant removal

Saroj Raj Kafle^{a,†}, Sangeet Adhikari^{b,†}, Rakesh Shrestha^c, Sagar Ban^c, Gaurav Khatiwada^c, Pragati Gaire^c, Nerisha Tuladhar^c, Guangming Jiang^d and Ananda Tiwari^{IWA ib e,f,*†}

^a Department of Chemical Engineering, Texas A&M University, College Station, TX, USA

^b School of Sustainable Engineering and the Built Environment, Tempe, AZ 85281, USA

^c Department of Chemical Science and Engineering, Kathmandu University, P.O. BOX 6250, Dhulikhel, Kavre, Nepal

^d School of Civil, Mining, and Environmental Engineering, University of Wollongong, Wollongong, Australia

^e University of Helsinki, Faculty of Veterinary Medicine, Department of Food Hygiene and Environmental Health, Agnes Sjöbergin katu 2, Helsinki FI-00014, Finland

^f Department of Health Security, Water Microbiology laboratory, Finnish Institute for Health and Welfare, Kuopio, Finland

*Corresponding author. E-mail: ananda.tiwari@thl.fi

†Equally contributed to this work.

 AT, 0000-0001-8026-6885

ABSTRACT

In the face of growing global freshwater scarcity, the imperative to recycle and reuse water becomes increasingly apparent across industrial, agricultural, and domestic sectors. Eliminating a range of organic pollutants in wastewater, from pesticides to industrial byproducts, presents a formidable challenge. Among the potential solutions, membrane technologies emerge as promising contenders for treating diverse organic contaminants from industrial, agricultural, and household origins. This paper explores cutting-edge membrane-based approaches, including reverse osmosis, nanofiltration, ultrafiltration, microfiltration, gas separation membranes, and pervaporation. Each technology's efficacy in removing distinct organic pollutants while producing purified water is scrutinized. This review delves into membrane fouling, discussing its influencing factors and preventative strategies. It sheds light on the merits, limitations, and prospects of these various membrane techniques, contributing to the advancement of wastewater treatment. It advocates for future research in membrane technology with a focus on fouling control and the development of energy-efficient devices. Interdisciplinary collaboration among researchers, engineers, policymakers, and industry players is vital for shaping water purification innovation. Ongoing research and collaboration position us to fulfill the promise of accessible, clean water for all.

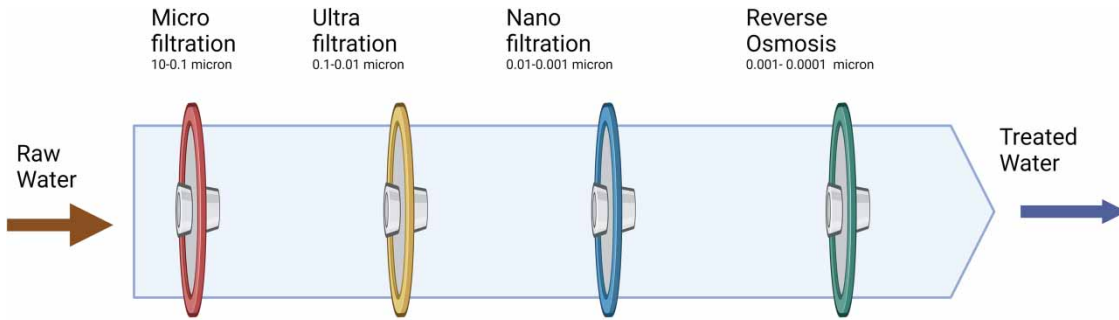
Key words: fouling mechanisms, membrane technologies, organic contaminant removal, wastewater treatment

HIGHLIGHTS

- Effective wastewater treatment helps to recycle and reuse water.
- Membrane technologies are promising for treating wide organic contaminants.
- This paper explores various advanced membrane techniques.
- This review examines membrane fouling, including influencing factors and prevention strategies.
- It illuminates the evolving membrane techniques, aiding the progress of wastewater treatment.

This is an Open Access article distributed under the terms of the Creative Commons Attribution Licence (CC BY 4.0), which permits copying, adaptation and redistribution, provided the original work is properly cited (<http://creativecommons.org/licenses/by/4.0/>).

GRAPHICAL ABSTRACT

**Membrane separation technologies**

- Microfiltration
- Membrane bioreactor
- Nanofiltration
- Reverse osmosis
- Membrane Distillation
- Pervaporation
- Forward osmosis
- Liquid membrane

Benefits

- Filter wide range of pollutants
- Ecological
- Low sludge
- Scalable
- Adaptable

Used to treat

- Suspended solids
- Microbes biological pollutants
- Carbon and phosphorus
- Dyes and colors
- Cellulose and fibrous materials
- Iron and manganese
- Organic compounds
- Pharmaceuticals and personal care products
- Salts and minerals
- Oil and grease
- Volatile organic compounds

ABBREVIATIONS

AMD	acid mine drainage system
BLM	bulk liquid membrane
CA	cellulose acetate
CNC	cellulose nanocrystal
COD	chemical oxygen demand
CTA	cellulose triacetate
DCMD	direct contact membrane distillation
DMF	dimethylformamide
DMSO	dimethyl sulfoxide
EGDMA	ethylene glycol dimethylacrylate
ELM	emulsion liquid membrane
EPS	extracellular polymeric substances
FO	forward osmosis
FOMBR	forward osmosis membrane reactor
FOwEO	forward osmosis with the function of electrochemical oxidation
FTIR	Fourier transformation infrared spectroscopy
GO	graphene oxide
IBU	Ibuprofen
LAS	linear alkylbenzene
LM	liquid membrane
MBR	membrane bioreactor
MCE	mixed cellulose ester
MDP	m-phenylenediamine
MF	microfiltration
NF	nanofiltration
NMP	N-methyl pyrrolidone
OSRO	reverse osmosis organic solvent
PA	polyamide
PAFO	pressure-assisted forward osmosis
Pd	palladium
PDMS	polydimethylsiloxane

PE	polyethylene
PEGDA	polyethylene glycol diacrylate
PEI	polyethyleneimine
PES	polyether sulfone
PK	polyketone
PV	pervaporation
PVDF	polyvinylidene
RSF	reverse salt flux
RSM	response surface methodology
RO	reverse osmosis
SA	salicylic acid
SGMD	sweep gas membrane distillation
SLM	supported liquid membrane
SRSF	specific reverse salt flux
TBP	tributyl phosphate
TDA	tridodecylamine
TDS	total dissolved solids
TFC	thin film composite
TFN	thin-film nanocomposites
TOC	total organic carbon
TrOC	trace organic compound
TSS	total suspended solids
WWTP	wastewater treatment plant
XRD	X-ray diffraction

1. INTRODUCTION

Membrane separation technology (MST) is promising for selectively removing various organic pollutants from diverse sources through a semi-permeable membrane (Nqombolo *et al.* 2018; Obotey Ezugbe & Rathilal 2020; Bera *et al.* 2022). This technology is promising for removing a range of physical, biological, and chemical pollutants. It serves as a cost-effective and ecological wastewater treatment solution, notable for its minimal chemical usage and absence of hazardous byproducts (Jacangelo *et al.* 1997). Consequently, MST contributes to safeguarding public health and the environment by reducing exposure to harmful organic pollutants (Guo *et al.* 2019).

Selecting an appropriate membrane type, influenced by pollutant size properties and wastewater characteristics, is the primary step in MST for removing organic pollutants (Lee *et al.* 2016; Dai *et al.* 2019; Subramaniam *et al.* 2019; Ahmed *et al.* 2021; Ren *et al.* 2021; Rout *et al.* 2021). For instance, a hydrophobic membrane can effectively remove biocides and bacterial organic particles (Shahid *et al.* 2021). This technology provides an economical, sustainable, and efficient wastewater treatment method. It produces low sludge, is eco-friendly, scalable, adaptable to different environments, and can be integrated with other treatment methods for enhanced efficiency (Singh & Hankins 2016). It is scalable, adaptable to various environments, and can be integrated with other treatment methods to enhance removal efficiency.

Various organic pollutants, such as volatile organic compounds (VOCs) – including gaseous or liquid-phase compounds such as solvents, chemical precursors, intermediates, and petroleum compounds – can be present in wastewater. These substances are typically released from solvents, fuels, and other chemicals. Similarly, polycyclic aromatic hydrocarbons, another type of organic pollutant, form through the incomplete combustion of materials such as coal, oil, and gas. Another category of organic pollutants in wastewater is pharmaceuticals and personal care products (PPCPs). These include commonly used substances such as antibiotics, hormones, and fragrances, which enter wastewater through urine and feces (Gaur *et al.* 2018). PPCPs, including substances such as antibiotics, hormones, and fragrances used in daily life, can end up in wastewater through urine and feces. Pesticides, utilized in agriculture for pest and disease control, can be released into the environment via runoff, leaching, and spray drift (Wolf *et al.* 1991). Similarly, chlorinated solvents, used in industrial processes such as dry cleaning and metal cleaning, can enter the environment through spills, leaks, and improper disposal. Dioxins and furans, toxic byproducts of certain industrial processes such as waste incineration and chemical manufacturing, can also form during forest fires and volcanic eruptions. Proper wastewater treatment processes are essential to mitigate the adverse effects of these pollutants and protect both human health and the environment (Garcia-Rodríguez *et al.* 2014).

Various membrane types, including polymeric, ceramic, and composite membranes, have been evaluated for their potential to remove organic pollutants to advance membrane bioreactors (MBRs), forward osmosis (FO), and other applications (Warsinger

et al. 2018). However, a comprehensive understating of the removal of organic contaminants, and their complex interactions with membrane materials and the surrounding environment is lacking (Khan & Ghoshal 2000; Farahbakhsh *et al.* 2004; Huang *et al.* 2009; Li & Visvanathan 2017; Malkoske *et al.* 2020). These limitations pose challenges in scaling up MST from laboratory scale to practical applications. While attempts have been made to optimize these limitations, studies conducted in diverse settings with different pollutants and conditions make it challenging to draw concrete comparisons (Lee *et al.* 2016; Dai *et al.* 2019; Subramaniam *et al.* 2019; Ahmed *et al.* 2021; Ren *et al.* 2021; Rout *et al.* 2021). The next significant challenge in this field is addressing fouling and membrane degradation to broaden the utilization of MST (Sayan *et al.* 2013).

Previous MST research for organic pollutant removal primarily aimed at optimizing membrane selectivity and permeability (Yang & Yang 2022), optimizing operating conditions to enhance separation efficiency (Gan *et al.* 2023), and understanding pollutant transport mechanisms through membranes (Ren *et al.* 2021). Additional studies explored the application of nano-filtration and reverse osmosis (RO) membranes to eliminate pharmaceuticals and endocrine disruptors (Riley *et al.* 2016). Research also delved into developing hybrid membrane systems for treating oil and gas-produced water and utilizing MBRs for industrial wastewater treatment (Riley *et al.* 2016).

Organic pollutants can be separated through physical, biological, or chemical processes. Physical separation can be a better option among these, especially when compared to biological degradation, which can be complex due to the potential toxicity of organic pollutants (Hanafi & Sapawe 2020). While chemical processing could be a viable alternative, offering a solution for eliminating organic and inorganic matter, color, and recalcitrant substances, it can be more expensive and falls beyond the scope of the current study (Hanafi & Sapawe 2020). This study aims to (a) evaluate the effectiveness of various membrane technologies for removing organic pollutants removal, identifying their respective advantages and limitations, (b) investigate novel pre-treatment methods to minimize fouling, enhance membrane durability, and devise strategies for improving membrane selectivity towards specific organic pollutants while maintaining high permeability. The insights gained from this review can aid researchers and engineers in developing membrane-based treatment systems, effectively eliminating organic pollutants from diverse wastewater types and contributing to environmental protection.

2. MEMBRANE TECHNOLOGY TYPES

In recent decades, various physical separation-based MSTs have gained popularity for their advantages in water and wastewater treatment (Quist-Jensen *et al.* 2015). However, membrane fouling remains a challenge despite these benefits, especially with highly soluble contaminants. This chapter deals with the various physical separation MSTs, emphasizing their applications and challenges.

2.1. Microfiltration

Microfiltration (MF) is widely used in diverse industries such as pharmaceuticals, food and beverages, and semiconductors, for effective wastewater treatment (Baker 2012). This process uses filter pore sizes from 0.1 to 10 μm to eliminate pollutants such as sediment, algae, protozoa, bacteria, and proteins (Baker 2012). However, MF cannot remove tiny colloids, viruses, natural organic matter, and ions that surpass its filter retention capabilities (Howe *et al.* 2012).

Membrane materials in MF are selected for high mechanical strength, film-forming properties, good thermal and chemical stability, and stability over a wide pH range (Urošević & Trivunac 2020; Gul *et al.* 2021). Notably, a cementitious membrane effectively removes small organic pollutants, showcasing a significantly improved reaction rate constant compared to stand-alone ozone oxidation. Additionally, the membrane demonstrates good retention efficiency at low trans-membrane pressure (Sun *et al.* 2021).

MF transports suspended liquids through a sheet or tubular configuration, either parallel or perpendicular to the semi-permeable membrane (Figure S1). This process occurs at reasonably high velocities, typically in the 1–3 m/s range, and under low to moderate pressures, usually around 100–400 kPa (Green & Southard 2019). A pump, either vacuum-driven or pressure-driven, serves as the processing equipment, facilitating the liquid flow through the membrane filter. To monitor the pressure differential between the inlet and outlet streams, a differential or standard pressure gauge is frequently installed (Baker 2012).

Hybrid systems, such as integrating photocatalysis and membrane MF functionalities, reduce membrane fouling and enhance permeate flux, reporting efficiency increases of up to 10% (Ho *et al.* 2010; Zhao *et al.* 2020). Another noteworthy hybrid system combines MF with biological treatment using a mixed cellulose ester membrane, effectively resulting chemical oxygen demand (COD), total organic carbon (TOC), and phenols (Mameda *et al.* 2020). Furthermore, electrochemical MF is effective in removing COD, nitrogen, organic carbon, color, turbidity, and fluorophores (Mameda *et al.* 2020). In a separate

development, a reactor combining electro-oxidation with a boron-doped diamond (BDD)/Ti anode and ceramic membrane MF was created to simultaneously remove soluble and particulate organic matter from wastewater, achieving complete COD removal and 90% removal of color and turbidity from dye wastewater (Juang *et al.* 2013).

MF is a potent wastewater treatment method, yet certain limitations merit consideration (Table 1). Common drawbacks include fouling, susceptibility under harsh chemical, thermal, or mechanical conditions, and relatively low durability. Moreover, MF can be costly due to three major factors: sintering temperature, membrane materials, and preparation procedures. Reducing the cost of MF is an important but challenging, as altering sintering temperature and preparation procedures may prove difficult. However, developing cost-effective raw materials for membranes can help mitigate overall costs (Singh & Purkait 2019).

2.2. Membrane bioreactor

MBR is an emerging wastewater treatment technology utilizing low-pressure membrane filtration to separate effluent from activated sludge (Jefferson *et al.* 2000). This approach combines a biological wastewater treatment process, such as the activated sludge process, with a membrane process, including MF or ultrafiltration (Figure S2). MBR has two primary configurations: the submerged membrane bioreactor (SMBR) and the side-stream MBR (Goswami *et al.* 2018). In SMBRs, the membrane is within the biological reactor and submerged in the wastewater, while in the side-stream MBR, the membrane is positioned outside the reactor as an additional step following biological treatment (Goswami *et al.* 2018).

In an MBR system, membranes with pore sizes between 0.035 and 0.4 μm are immersed in an aerated biological reactor (van't Oever 2005). This eliminates the need for sedimentation and filtration processes common in wastewater treatment, enabling the biological process to operate at a higher mixed liquor concentration, thereby reducing the required process tankage. The mixed liquor is typically maintained at 1.0–1.2% solids, ensuring optimal aeration and scouring around the membranes, a concentration four times higher than conventional plants (van't Oever 2005).

Table 1 | Some applications of microfiltration (MF) membranes

Membrane material	Source of wastewater	Removal efficiency (%)	Membrane properties	Merits	Demerits	References
Electrodeposited CuO/carbon membrane (DECuO/C)	Laboratory analysis	RhB = 99.96; COD = 71.82; TOC = 64.29	Permeability = 823.03 L/($\text{m}^2 \cdot \text{h} \cdot \text{bar}$)	An approach to preparing high-performance electrocatalytic membrane	Pollutants smaller than membrane pores are difficult to remove	Li <i>et al.</i> (2020)
Integrated biological-ceramic membrane	Industries such as pulp and paper, biomass gasification, and dairy	COD (pulp and paper) = 92.7; COD (biomass gasification) = 87.6; COD (dairy) = 88.2	Porosity = 44%, pore diameter = 1 μm	Cost-effective approach		Goswami <i>et al.</i> (2019)
PVDF	Greywater	COD = 98.22; LAS = 99.97; TSS = 99.99; turbidity = 99.98	Pore size = 0.1 μm ; membrane area = 0.2 m^2 ; membrane length = 50 cm	The combination of multi-layer slow sand filter, MF, and ultrafiltration is more effective for LAS and suspended solids	An increase in organic loading rates decreases the removal efficiency	Babaei <i>et al.</i> (2019)
Aluminosilicate composite	Laboratory analysis	Benzophenone-4 = 100; TOC = 52.67	Pore size = 1.33–0.15 μm	Low cost non-toxic, good mechanical strength with a large pore-size membrane material	Mechanical strength was affected by changes in different parameters	Sun <i>et al.</i> (2021)

COD = chemical oxygen demand, LAS = linear alkylbenzene, TSS = total suspended solids, TOC = total organic carbon.

MBR technology, with its clear advantages over conventional methods, has clear advantages over conventional methods, and it is widely used in diverse industrial wastewater treatment applications (Table 2). Employing membrane filtration units to replace the secondary settler provides several benefits compared to traditional approaches (Lin *et al.* 2012). This allows effective treatment of dense wastewater, including industrial effluents and landfill leachate (Van Dijk & Roncken 1997).

Comparative studies between MBRs and conventional activated sludge systems for micropollutant degradation reveal shorter lag phases and stronger memory effects in MBRs. This suggests a quicker response to variable influent concentrations and reduced sensitivity to operational variables (De Wever *et al.* 2007). In an experiment focusing on removing alkyl phenol ethoxylates and their degradation products, linear alkylbenzene (LAS) sulfonates, and coconut diethanol amides, an MBR was evaluated alongside a full-scale wastewater treatment plant employing conventional activated sludge (González *et al.* 2007). The MBR exhibited a 94% efficiency in retaining and degrading alkyl-phenolic compounds, contrasting with the conventional activated sludge treatment's 54% removal of total nonylphenol compounds (González *et al.* 2007).

In an experiment exploring mixed liquor pH impact (ranging from pH 5 to 9) on trace organics removal in a submerged MBR system, results showed notable pH-related effects on ionizable trace organics, such as sulfamethoxazole, ibuprofen, ketoprofen, and diclofenac. Higher removal efficiencies were evident at pH 5 due to enhanced adsorption to activated sludge (Tadkaew *et al.* 2010). A subsequent study examined the degradation of 3 estrogens, 2 endocrine disruptors, and 10 pharmaceutical substances in a membrane separation bioreactor. Lower pH operation correlated with increased removal rates of acidic pharmaceutical substances, primarily attributed to heightened adsorption to sludge particles (Urase *et al.* 2005).

Despite the numerous advantages of MBRs over conventional methods, membrane fouling poses a significant challenge, reducing productivity and increasing maintenance and operating costs. This fouling can manifest on the membrane surface or within the membrane pores, being reversible (removable by physical washing) or irreversible (requiring chemical cleaning). Researchers highlight extracellular polymeric substances (EPS), specifically the carbohydrate fraction from the soluble microbial product (soluble EPS or biomass supernatant), as a key fouling factor in MBRs. Various strategies, such as adjusting hydrodynamics and flux, optimizing module design, and manipulating bioreactor conditions, have been proposed to control fouling (Le-Clech *et al.* 2006).

2.3. Reverse osmosis

RO stands out as an advanced membrane filtration method that employs a semi-permeable membrane to effectively eliminate ions, molecules, larger particles, and various dissolved and suspended contaminants, including viruses (Ouyang *et al.* 2019). This process relies on applying pressure to counteract osmotic pressure (Figure S3), typically ranging from 17 to 27 bars for

Table 2 | Various applications of filtration membrane

Industry	Applications	References
Food and beverage	<ul style="list-style-type: none"> • Concentration and nutritional enrichments of food products • Control of alcohol content of wines partial sugar removal from musts • Reduction of volatile acidity in wines acidification of wines • Removal of phenolic compounds from pomegranate juice 	Abdel-Fatah (2018), Mulyanti & Susanto (2018), Nath <i>et al.</i> (2018)
Textile and dyes	<ul style="list-style-type: none"> • Concentration • Permeation of organic salts • Removal of color • Removal of reactive dyes, salts, dye intermediates from wastewater 	Abdel-Fatah (2018), Nath <i>et al.</i> (2018), Tavangar <i>et al.</i> (2019)
Industrial process and wastewater	<ul style="list-style-type: none"> • Remove wastewater and semi-volatile organic compound from industrial process • Removal of degreasing agents from wastewater • Removal of organic pollutants such as pesticides 	Abdel-Fatah (2018), Nath <i>et al.</i> (2018)
Biotech and pharmaceuticals	<ul style="list-style-type: none"> • Separation, concentration, recovery, and production of hormones 	Abdel-Fatah (2018), Kyburz <i>et al.</i> (2021)

brackish water and 52 to 69 bars for seawater. Osmotic pressure, a colligative property driven by differences in the chemical potential of the solvent (Table 3), propels this mechanism. Diffusion serves as the primary force for organic liquid separation and overcoming the formidable osmotic pressure barrier (Liu *et al.* 2021a).

Effectively separating molecules smaller than 100 Da poses a considerable challenge, especially in pursuing an energy-efficient membrane technology for organic molecule separation. The swelling issue is significant in RO separation, particularly when dealing with organic solvents with a molecular weight below 100 Da.

In general, chemically and thermally stable cellulose is extracted from plants, while living organisms are employed in RO (Abdel-Fatah 2018). Improving the anti-fouling properties of the RO cellulose membrane involved incorporating cellulose nanocrystals into the polyamide (PA) thin-film nanocomposites membrane through in-situ polymerization of *m*-phenylenediamine and trimethyl chloride. This enhancement was confirmed through X-ray diffraction and Fourier transformation infrared spectroscopy analysis (Asempour *et al.* 2018).

For the separation of methanol and isobutanol from wastewater, a uniform cellulose membrane exhibited higher adsorption of methanol compared to isobutanol (Liu *et al.* 2021a). A cellulose acetate (CA)/graphene oxide (GO) nanocomposite membrane was prepared using the plane inversion method. Increasing the GO concentration up to 1 wt.% improved mechanical properties due to physiochemical interactions with the CA matrix. However, a further increase in concentration adversely affected membrane separation (Ghaseminezhad *et al.* 2019).

A subsequent study evaluated the removal efficiency of ultra-trace organic compounds (TrOCs) by a hollow fiber cellulose triacetate (CTA) RO membrane. The reported removal efficiency was similar to that of PA membranes, with molecular size significantly influencing the removal process (Fujioka *et al.* 2015).

A reverse osmosis organic solvent (OSRO) membrane was developed through interfacial polymerization on a polyketone (PK) support, achieved separation factor of 8.4 for methanol from the methanol/toluene mixture. To enhance selectivity and the separation factors, the simple heat treatment process, including initial oven heating followed by hot water heating, was applied (Liu *et al.* 2021b). Coating an organic-resistant substance on the PK support using a straightforward procedure resulted in an OSRO membrane with a flux of 1.0–4.0 km for non-polar liquids (alkane and toluene) and zero flux for polar liquids (alcohol) under 4 MPa (Liu *et al.* 2021b).

Utilizing a polyethylene (PE) support, a highly selective and mechanically durable PA thin-film composite (TFC) reverse osmosis (RO) membrane was prepared. The TCE-PE membrane exhibited superior mechanical and organic solvent resistance properties compared to commercial membranes (Park *et al.* 2018). Benzyl alcohol (BA) enhanced the separation performance of PA RO membranes, with BA-activated RO membranes showing higher water performance and perm selectivity than commercial membranes (Shin *et al.* 2019).

Silica significantly improved the properties of polyethylene glycol membranes in RO, improving both hydrophilicity and fouling resistance (Ahmad *et al.* 2015). After activating various concentrations of polyethylene glycol diacrylate and ethylene glycol dimethacrylate with sodium hypochlorite for 1 h, a TFC-RO membrane with high performance, and lower organic fouling was prepared (Kavaiya & Raval 2022). Addressing the challenging removal of boron from seawater, UiO-66 nanoparticles were doped into a PA thin-film nanocomposite RO membrane. This doping improved boron rejection by 11% compared to benchmark membranes (Liu *et al.* 2019).

While RO offers numerous advantages over other membrane techniques, it is essential to consider major drawbacks such as low permeation flux, inadequate selectivity, limited membrane durability, membrane fouling, and high equipment and

Table 3 | Estimated osmotic pressures for various organic solvent

Organic liquid name	Estimated osmotic pressure (bar)
NMP/Toluene	21.93
DMF/Toluene	29.63
DMSO/Toluene	27.99
DMSO/Toluene	26.31
NMP/Methanol	20.26

NMP = N-methyl pyrrolidone, DMF = dimethylformamide, DMSO = dimethyl sulfoxide.

operational costs (Wenten 2016). Addressing these challenges involves combining co-solvent interfacial polymerization and surface modification of substrates and active layers in RO membranes (Hailemariam *et al.* 2020).

2.4. Nanofiltration

Nanofiltration, an advanced membrane technology, is used for water and wastewater treatment and efficient recovery of divalent metals (Butterworth 2010). This technique utilizes a semi-permeable organic membrane under pressure to separate substances. The membranes have ultra-small pores, typically ranging from 0.1 to 10 nm, often around 1 to 2 nm in size, and with a molecular weight range of 100–5,000 Da (Nath 2017).

Nanofiltration membranes represent a versatile separation technology with properties lying between those of ultrafiltration and RO membranes (Figure S4). The separation process in nanofiltration hinges on differences in particle size and charge effects, particularly for ionic components (Mulyanti & Susanto 2018). Physical sieving emerges as a dominant mechanism for components with high molecular weight (Shon *et al.* 2013).

Nanofiltration membranes can be produced through polymer phase inversion, resulting in uniform asymmetric membranes, or via interfacial polymerization, where a TFC layer is added to an ultrafiltration membrane substrate (Table 4). Common materials for homogeneous asymmetric nanofiltration membranes include CA and sulfonated polysulfone. TFC nanofiltration membranes utilize cross-linked PA polymers with charged 'pendants,' and typical substrate materials include polysulfone, polyether sulfone (PES), polyvinylidene fluoride (PVDF), polyacrylonitrile, and polyether ether ketone.

To withstand extreme conditions such as low or high pH, high temperatures, or organic solvent environments, highly cross-linked nanofiltration membranes have been developed, featuring a slightly charged surface (Van der Merwe 1998). Key characteristics include low rejection of monovalent ions, high rejection of divalent ions, and high flux when compared to ultrafiltration and RO membranes (Marchetti *et al.* 2014; Mohammad *et al.* 2015).

In a previous study, the diffusion phenomenon was evaluated through molecular dynamic simulation of eight monosaccharides. The study found that the interaction force between the membrane and monosaccharides followed the order of sorbose > fructose > glucose > mannose > galactose, and ribose > xylose > arabinose. Additionally, the diffusion coefficient of the monosaccharides inside the membrane was found to be in the order sorbose > galactose > glucose > mannose > fructose > ribose > xylose > arabinose (Yao *et al.* 2018). Membrane performances are significantly influenced by operating conditions such as temperature, operating pressure, flow rate, membrane characteristics, and feed characteristics (Mulyanti & Susanto 2018).

Table 4 | Common membrane types used in nanofiltration

Membrane	Efficiency	Drawbacks	Advantage	Reference
Polymeric membrane	High	Limited thermal and solvent stability	<ul style="list-style-type: none"> • Cost-effectiveness, excellent process ability, good reproducibility, and versatility 	Lim <i>et al.</i> (2017)
Cellulose-based membrane	High	Shorter life span, low resistance to membrane fouling, low chemical resistance, weak high-temperature resistance	<ul style="list-style-type: none"> • High strength, high specific surface area, high surface activity, non-toxic, renewable 	Liu <i>et al.</i> (2021c)
TFC membrane	High	Impossible for large-scale production, high cost	<ul style="list-style-type: none"> • High yield • Energy efficient • High selectivity • High water permeability 	Voicu & Thakur (2021); Seah <i>et al.</i> (2020)
Ceramic membrane	Medium	Inflexible, high investment cost, low degradability, less selectivity, high energy consumption	<ul style="list-style-type: none"> • High thermal stability • High chemical resistant • High pressure • Long life • Less contaminated 	Liu <i>et al.</i> (2021c)
Metallic oxide membrane	Medium	High raw material cost	<ul style="list-style-type: none"> • High water permeability • More effective for removing bacterial particles 	Yang <i>et al.</i> (2019); Sonawane <i>et al.</i> (2021)

Fouling is a significant challenge in the nanofiltration process, resulting in decreased flux and diminished cost efficiency over time. It arises from various soluble and suspended materials, including colloids, organic and inorganic substances, as well as biological components (Mohammad *et al.* 2015). To mitigate fouling, various physical, chemical, and hydrodynamic methods can be employed (Table 6). Notably, the acid mine drainage (AMD) system has proven effective in removing organic fouling in nanofiltration membranes, with hydrochloric acid (HCl) solutions being particularly efficient in addressing AMD-related fouling issues (Juholin *et al.* 2018). The utilization of graphene-based membranes and the incorporation of nano-materials shown significant promise in reducing membrane fouling in organic nanofiltration processes (Nie *et al.* 2021). However, further studies are needed for even more efficient and effective fouling control (Mohammad *et al.* 2015).

2.5. Membrane distillation

Membrane distillation (MD) is a promising, thermally driven separation technology utilizing a porous hydrophobic membrane that allows passing of vapor molecules (Figure S5). The pressure difference across the membrane surfaces serves as the driving force (A Shirazi & Kargari 2015). MD is applied in diverse fields, including desalination of both seawater and brackish water, treating radioactive waste, and removing organics and heavy metals from wastewater (Alkhubiri *et al.* 2012). The MD process encompasses four configurations: direct contact membrane distillation (DCMD), air gap MD, vacuum MD, and sweep gas MD. Notably, DCMD, the most common configuration, is applied in various wastewater treatment applications targeting organic pollutants (Curcio & Drioli 2005).

Unlike conventional thermal distillation, MD operates at a lower temperature, driven by a non-exclusively thermal force. The hydrophobic membrane prevents the entry of aqueous solutions into pores, establishing liquid/vapor interfaces only under a trans-membrane pressure surpassing the membrane's liquid entry pressure. Consequently, three stages define water transport through the membrane: (1) formation of a vapor gap at the interface between the hot feed solution and the membrane, (2) transportation of the vapor phase through the microporous system, and (3) condensation of vapor at the interface between the cold side of the membrane and the permeate solution (Onsekizoglu 2012).

The MD process offers significant advantages, operating at lower temperatures than conventional methods and requiring lower hydrostatic pressure than pressure-driven technologies, enhancing cost-effectiveness. MD, a relatively new and energy-efficient process, stands out for its lower operational costs and energy consumption compared to conventional techniques such as distillation and RO (Drioli *et al.* 2015). The reduced energy consumption results from the lower required temperature compared to traditional distillation systems. Additionally, the process generates low-grade waste and its cost-effectiveness can be further enhanced by coupling it with alternative energy sources such as solar, geothermal, and photo energy. The lower feed temperature in MD necessitates a relatively lower driving force, which does not compromise process efficiency. Presently, MBRs coupled with MD systems have been developed for treating wastewater containing organic pollutants, addressing the limitations of MBRs. These applications extend beyond the lab scale and are implemented on a commercial scale as well.

Research on the potential application of MD systems for removing organic pollutants from diverse wastewater sources has garnered significant interest. In the case of coke wastewater, a MD system effectively produced permeates within discharge limits, allowing all refractory organics to pass the hydrophobic membrane (Ren *et al.* 2018). Similarly, the municipal wastewater containing TrOCs including pharmaceuticals, steroid hormones, industrial chemicals, and pesticides, underwent MD treatment. In an experiment, the MD system successfully removed all TrOCs with pH >9, while those with pH < 9 required coupling with a MBR for complete removal (Wijekoon *et al.* 2014). This underscores the significant impact of pH and coupling on the MD system's efficiency. Notably, recent applications of coupling the MD system with other technologies are shown in Table 5.

Persistent phenolic compounds such as nitrophenol, chlorophenol, and bisphenol pose environmental hazards with prolonged toxic effects on humans and animals. An effective method for their removal is the direct contact MD process, showcasing a removal efficiency exceeding 80% (Ramos *et al.* 2021). Additionally, the separation of oil from water, particularly from petrochemical and oil and gas industries, is achieved through various methods such as dissolved air flotation, gravity and skimming, coagulation and flocculation, and hydrocyclone techniques. However, membrane-based methods stand out for stable emulsified oily wastewater due to their advantages, such as high oil removal efficiency, low operation cost, high-quality effluents, and scalability. Implementation of the membrane treatment process requires a pre-treatment process to remove or degrade organics (Han *et al.* 2017). A hybrid system, coupling MD with a two-stage pre-treatment process (oil/water separation and photocatalytic organic degradation), was developed for petrochemical wastewater treatment

Table 5 | Problems and preventions of various membrane technology

Membrane technology	Problem	Prevention	References
RO	Precipitation of iron	Backwashing cleaning process with citric acid (0.01%) as a cleaning reagent	Melliti <i>et al.</i> (2019)
Nanofiltration	Acid mine drainage due to oxidation of sulfide minerals	Chemical cleaning with 0.20% w/w hydrochloric acid (HCl)	Aguiar <i>et al.</i> (2018)
MD	Membrane scaling by inorganic crystals and membrane fouling by organic matter in feed solutions	Development of robust and super hydrophobic membrane via electro-spinning followed by electrospray to enhance membrane anti-wetting properties	Liao <i>et al.</i> (2020)
MBRs	Biofilm formation (bio fouling) induced via cell-to-cell communication (quorum sensing)	Bacterial quorum quenching along with physically (permeate) and chemically (chlorine) enhanced backwashing	Weerasekara <i>et al.</i> (2016)
Ultrafiltration	Membrane fouling caused by effluent organic matter	Ultraviolet-based oxidation pre-treatments (ultraviolet/persulfate (UV/PS) and ultraviolet/hydrogen peroxide (UV/H ₂ O ₂))	Qu <i>et al.</i> (2021)

Table 6 | Applications of coupling the membrane distillation (MD) system with other technologies

System integrated with	Pollutants	Parameters	Results	References
Photocatalysis	4-chlorophenol (4-CP) and Ag ⁺ ion	Usage of BiOBr films	Degradation of 4-CP and 95% Ag ⁺ ion removal	Zou <i>et al.</i> (2020)
Homogeneous catalytic ozonation	TOC and salt	Temperature (327 K)	TOC (98.6%) and salt (100%)	Zhang <i>et al.</i> (2016)
Anaerobic MBR	Bulk organic matter and phosphate	Temperature (318 K)	100% removal efficiency compared to 76% by conventional MD	Song <i>et al.</i> (2018)
FO	TrOCs	Temperature (313 K)	Greater than 99.5% removal efficiency	Xie <i>et al.</i> (2013)
Electrochemical oxidation	VOCs	Temperature (343 K)	Decompose organics that MD alone could not and remove excess inorganic ions	Shin <i>et al.</i> (2020)
Osmotic MBR	TrOCs	Temperature (298 K)	Greater than 90% removal efficiency	Luo <i>et al.</i> (2017)
Anaerobic osmotic MBR	Pharmaceutically active compounds	Temperature (318 K)	The removal efficiency of 97.2% for dissolved organics	Arcanjo <i>et al.</i> (2021)
FO and electrocoagulation	Organic carbon from high-salinity brines	Temperature (333 K)	TOC (78%) and total suspended solids (96%)	Sardari <i>et al.</i> (2019)

(Table 6). Utilizing TiO₂ P25 as the photocatalyst for organic compound decomposition and microorganism inactivation, the two-stage pre-treatment process achieved a remarkable 99.5% organic degradation. In the first cycle, the system exhibited a 92% oil rejection, aiming to prevent MD fouling and reduce the production of volatile organics challenging to remove with traditional methods (Li *et al.* 2019). Integrating photothermal active nanoparticles for localized water heating can further reduce the overall system cost (Said *et al.* 2020).

2.6. Pervaporation

Pervaporation (PV), a membrane separation technique combining permeation and evaporation, selectively removes volatile compounds through a permeable membrane, diffusing them to the opposite sides (Figure S6). The receiving side, equipped with a vacuum or the purge gas, facilitates the separate collection of removed compounds. Depending on the membrane's selectivity, PV finds applications in dehydrating organic solutions or removing organic contaminants from wastewater. Its

extensive application spans diverse fields, including petrochemicals, food, biotechnology, pharmaceuticals, desalination, and various industrial sectors, offering higher separation capabilities and potential energy savings of 40–60% (Sekulić *et al.* 2005). The efficiency of the PV process hinges on the selectivity of the membrane. Recent advancements have led to investigating and developing various membrane types, including polymers, ceramics, and composites (De Bruijn *et al.* 2003). Polymer membranes, widely accepted, possess unique functionalities such as energy conversion, substance recognition and separation, superior permeation and flux, and efficient substance transfer.

Various polymeric membranes, including polydimethylsiloxane (PDMS), have been developed for PV separation in organic wastewater treatment. In a PV process targeting cyclohexane-containing wastewater, a PDMS membrane demonstrated a remarkable separation factor of 2,500 under operating conditions of 300 K temperature and a vacuum pressure of 10 mmHg (Rezakazemi *et al.* 2018). PV membrane separation is a widely used for ethanol/water separation. The integration of a PDMS membrane with the fermentation process holds promise for efficient bioethanol production. Testing the PDMS polymer membrane involved removing ethanol from water through integrated PV with batch ethanol fermentation. This system can be coupled with mechanical vapor compression for enhanced performance (Fan *et al.* 2017). With a separation factor ranging from 8 to 11.6, the integrated process demonstrated a high ethanol production rate on the permeate side of the membrane. This environmentally friendly and energy-saving approach holds promising prospects for long-term operation (Fu *et al.* 2016).

Phenolic compound mass transfer is reduced in membranes such as PDMS and urethane during PV separation of phenol-containing mixtures. To address this, alternative membranes have been devised to enhance separation efficiency and permeability. Cao *et al.* explored phenolic compound separation in an aqueous solution using a poly(ether-b-amide) (PEBA) PV membrane at 30–70 operating conditions. Both permeation flux and enrichment factor rose with temperature, while the enrichment factor declined with higher feed concentration (Cao *et al.* 2021). A PEBA membrane and a PVDF membrane were developed to recover high-purity aniline from an aqueous solution. The impact of feed concentration and temperature on separation performance was examined. At 80°C and a 3 wt.% feed concentration, the membrane exhibited outstanding performance, achieving 65.1% purity of aniline and a separation factor of 35. Scaling up this process should be considered, as it proves to be an effective method for separating high-boiling-point organic compounds from aqueous solutions (Wang *et al.* 2021a). When using the PDMS membrane alone, the removal efficiency of acetonitrile from the aqueous solution was only 47%. High salt in water positively influenced PV performance and the separation factor (Wang *et al.* 2018).

The PV process efficiently separates compounds forming azeotropes. Introduced in 1976 (Aptel *et al.* 1976), gained wide acceptance for azeotropic mixture separation research. A hybrid PV-distillation system was designed to reduce energy consumption in solvent recovery towers for ester/alcohol/water mixture. Compared to the traditional distillation system, the hybrid system cut annual cost by 36.03% (Li *et al.* 2022), proving more economical. PV-extractive distillation outperforms conventional methods for azeotropic mixtures. For challenging cyclohexane and isopropanol (IPA) azeotropes, combining distillation with PV lowers annual costs by 13.98% and CO₂ emissions by 15.09% (Zhang *et al.* 2021). Toth *et al.* explored a hybrid distillation-hydrophilic PV system for ethanol separation from pharmaceutical wastewater, achieving up to 99.5 wt. % purity (Toth *et al.* 2018). PV also excels in integration with photocatalysis; a PVDF membrane with photocatalytic TiO₂ rejected total dissolved solids (TDSs) at 2.345 mg/L and showed 98.02% color removal (Elma *et al.* 2022).

Various pathways, including membrane surface modification, enhance membrane separation. Introducing SiO₂ particles enhances membrane surface properties, expanding membrane technology applications in organic wastewater treatment. In a composite of PDMS/PVDF with SiO₂ particles, the separation factor was 2.5 times higher than a PDMS/PVDF membrane (Li *et al.* 2018a). Similarly, layering polyethyleneimine membranes with GO improved organic carbon rejection to 90.8%, enhancing flux rates. This suggests the promising use of GO as an incorporation material in PV membranes (Wang *et al.* 2021b).

2.7. Forward osmosis

FO effectively removes organic pollutants, even as small as 200 Da, such as pesticides, endocrine disruptors, and pharmaceutical molecules (Figure S7). These challenging separations for traditional membrane technologies are overcome by FO. Here, organic compounds move from the feed solution to the draw solution through a semi-permeable membrane, driven solely by the osmotic pressure gradient without external pressure (Madsen *et al.* 2015). FO exploits the natural tendency of water molecules to flow from low to high solute concentration across a semi-permeable membrane (Cath *et al.* 2006). The process involves a semi-permeable membrane separating a diluted feed solution from a concentrated draw solution,

allowing water flow while blocking solutes. The osmotic pressure gradient propels water from the feed to the draw solution, concentrating the feed and diluting the draw solution (Cath *et al.* 2006). The diluted draw solution produces pure water, while the concentrated feed solution undergoes contaminant removal. FO operates with either natural osmotic pressure or external pressure, the latter leveraging the solute concentration difference. External pressure on the draw solution enhances the concentration gradient, increasing water flux (Cath *et al.* 2006).

An experiment reported, FO effectively concentrated organic matter in sewage, so the COD in the concentrate increased by 300% (Zhang *et al.* 2014). Another study found FO to be more effective than RO in removing organic compounds such as phenol, aniline, and nitrobenzene from wastewater (Sauchelli *et al.* 2018). In RO, rejection of charged TrOCs involves electrostatic interaction and size exclusion, with increased molecular weight enhancing TrOC rejection (Alturki *et al.* 2013).

A forward osmosis membrane bioreactor (FOMBR) effectively removed Ibuprofen (IBU) as a TrOC, achieving average removal efficiencies exceeding 96.32% (Yao *et al.* 2021). Processes enhancing water production include pressure-assisted forward osmosis, which increased water production by 9 and 29% under applied pressures of 2 and 4 bar, respectively (Jamil *et al.* 2016). Furthermore, forward osmosis with electrochemical oxidation (FOwEO) was developed to reject trace antibiotics from the wastewater. In a nearly 3-h experiment, FOwEO exhibited over 98% rejection of antibiotics (Liu *et al.* 2015).

Commonly used membranes for FO include CA, polysulfone, PES, polysulfone, polybenzimidazole, and PA (Alsvik & Hägg 2013). A comparison between commercial CTA and TFC PA membranes was conducted to assess the rejection of pharmaceutical compounds (carbamazepine, diclofenac, IBU, and naproxen). TFC exhibited superior overall performance, featuring high water flux, excellent pH stability, and effective rejection of all targeted compounds compared to CTA (Jin *et al.* 2012). Whereas, TFC membranes were superior to CTA in various aspects such as water permeability, selectivity, flux, and swelling (Sauchelli *et al.* 2018). TFC outperformed CTA in water permeability, selectivity, flux, and chemical cleaning efficiency (Coday *et al.* 2015). Evaluation of CTA and TFC membranes for fouling and performance, considering water flux, reverse salt flux, and specific reverse salt flux, revealed steady performance for CTA after 1 week, while TFC showed variations (Bell *et al.* 2017).

Feed solution pH and draw solute significantly impact the filtration performance and rejection of the FO process. A study of model compounds such as cyclohexane carboxylic acid (CHA), 1-adamantane acetic acid (AAA), and a refined Merichem mixture of naphthenic acid (NA) revealed pH-dependent rejection for CHA and AAA (pH 3–9), while NAs exhibited a consistent 95% rejection unaffected by pH (Zhu *et al.* 2018).

The FO system offers major advantages, including high water permeability, solute rejection, water recovery rates, low fouling, and energy consumption, alleviating water supply stresses and promoting power generation (Ge *et al.* 2013). This system is effective in concentrating radioactive liquid waste in hospitals. FO outperforms ultrafiltration and RO in rejecting both natural and radioactive iodine, with a 99% rejection rate for oil from wastewater (Yadav *et al.* 2020).

A significant drawback of the FO process is the inefficient removal of small neutral organic compounds. This challenge can be addressed by employing biomimetic membranes, known for selectively rejecting only three TrOCs (Madsen *et al.* 2015). Another drawback is membrane fouling, but combining MD with FO membranes can mitigate the deposition of organic and particulate matter on the membrane surface, reducing fouling (Xie *et al.* 2013). Currently, all FO processes have been conducted on a benchmark scale with limited operation time. Thus, future studies ought to explore the technology in large-scale filtration processes (Blandin *et al.* 2020).

2.8. Liquid membrane

Liquid membrane (LM) technology utilizes liquid surfactant membranes in a drop column, offering high effectiveness in hydrocarbon separation. In this process, droplets of a hydrocarbon-containing feed solution are injected into an aqueous solution containing surfactants (Li 1968, 1978). LM transport combines liquid–liquid extraction and membrane separation into a single continuous device. It employs an extracting reagent solution immiscible with water, flowing between two aqueous solutions or gases known as the source (or feed) phase and the receiving (or strip) phase. Typically, the source and receiving phases are aqueous, while the membrane is organic, although the opposite configuration is possible. The membrane can be made of either a polymeric or inorganic microporous support, serving as a bearer (in supported liquid membrane (SLM)) or a barrier (in many bulk liquid membrane (BLM) technologies), or omitted entirely (in emulsion liquid membrane (ELM) and layered BLM).

Solute transport in the LM primarily relies on the solution-diffusion mechanism, where solute species dissolve in the LM and diffuse across it due to a concentration gradient. The efficiency and selectivity of transport can be enhanced by introducing a mobile complexation agent (carrier) into the LM, which reacts with the desired solute to form a complex. This process,

known as facilitated or carrier-mediated LM separation, is often combined with counter- or cotransport of different ions through LM to provide the energy for the uphill transport of the solute (Noble & Way 1987).

A thin gas or liquid film forms a barrier in the LM, separating two miscible liquids. Over the past two decades, LM technology has expanded its applications in chemical and pharmaceutical technology, biotechnology, food processing, and environmental engineering (San Román *et al.* 2010). Additionally, LM-based extractions can determine the concentration of freely dissolved pollutants on a time-weighted average basis, making them suitable for exposure risk assessment of metal ions in both environmental and biological samples (Chimuka *et al.* 2004). Moreover, the non-equilibrium mass transfer in the LM process offers advantages such as a greater driving force for mass transfer and minimal extractant quantity required (Li & Chen 2005). LM systems can also be automated and integrated with other separation techniques.

Phenols are commonly found in industrial wastewater and surface waters, posing environmental and health risks. An experiment using a SLM with tributyl phosphate (TBP) and sesame oil as the LM effectively extracted phenol under optimal conditions: 200 mg/L phenol concentration, 40% carrier concentration (%TBP), feed phase pH of 2, and stripping phase concentration of 1.1 M (Kazemi *et al.* 2014). Additionally, hydrophobic polypropylene membrane contactors, using Cyanex 923 as an extractant, achieved rapid phenol recovery, with a concentration ratio of approximately 39-fold and a 98% recovery rate (Reis *et al.* 2007). In the treatment of wastewater containing 1,050 mg/L nitrophenols, a LM process was employed, utilizing various parameters such as 2% surfactant concentration in the oil phase, 2% NaOH concentration in the internal water phase, a 2:1 ratio of oil phase to internal water phase, pH 2 in the external water phase, and a 3:1 ratio of external water phase to emulsion phase, resulting in a removal rate exceeding 99.99% for nitrophenols in wastewater (Luan & Plaisier 2004).

Efficient extraction of Palladium (Pd) from electroplating wastewater was achieved using a novel LM formulation with phosphonic acid groups as a carrier through the ELM process. Optimal conditions included 0.2 M Cyanex 302, 1.0 M thiourea in a 1.0 M H₂SO₄ stripping agent, 1:3 treatment ratio, pH 3 in the feed phase, and a 5-min extraction time, resulting in a maximum Pd extraction efficiency of 97% and a recovery of 40% (Othman *et al.* 2011).

Furthermore, chromium was successfully extracted from a wastewater solution containing waste sodium dichromate recovered from the pharmaceutical industry using the ELM technique. The LM consisted of kerosene oil as the solvent, SPAN-80 as the surfactant, potassium hydroxide as an internal reagent, and trioctylamine as the carrier. Response surface methodology optimization yielded the following conditions for optimal chromium extraction: a feed concentration of 224.04 ppm, pH 2.76, internal reagent concentration of 0.71 N, and a surfactant concentration of 1.92% (w/w), resulting in a maximum chromium extraction of 92.50% (Othman *et al.* 2011).

Additionally, an ELM was employed to extract Red 3BS reactive dye from an aqueous solution. Tridodecylamine (TDA) served as the carrier agent, salicylic acid (SA) was used to protonate TDA, sodium chloride acted as the stripping agent, and kerosene served as the diluent. SPAN 80 was utilized as an emulsifier. Under optimal conditions including 0.1 M SA, a 5-min extraction time, 3% (w/v) SPAN 80 concentration, 0.3 M NaCl concentration, 0.1 M TDA concentration, 350 rpm agitation speed, 12,000 rpm homogenizer speed, 10 min of emulsifying time, and a 1:15 emulsion to reactive dye solution ratio, nearly 100% removal of Red 3BS dye was achieved (Othman *et al.* 2011).

3. MEMBRANE FOULING

Membrane fouling stands as a significant challenge, greatly impeding the overall performance of membrane-based processes (Table 7). The accumulation of suspended solids, microorganisms, or organic substances within the membrane pores results in decreased permeate flux and the onset of membrane fouling. This fouling can manifest in various forms: (a) biological fouling stemming from the deposition and growth of biofilms on the membrane, (b) colloidal fouling caused by the buildup of microorganisms, biological detritus, polysaccharides, lipoproteins, clay, silt, oils, iron, and manganese oxides, (c) organic fouling due to the deposition of organic compounds, or (d) inorganic fouling (scale) brought about by the deposition of inorganic salts such as CaSO₄, CaCO₃, and SiO₂ on the membrane surface. The extent of membrane fouling is influenced by various factors, including feed characteristics such as pH and ionic strength, membrane properties such as roughness and hydrophobicity, and process conditions such as cross-flow velocity, trans-membrane pressure, and temperature (Shon *et al.* 2002; Obotey Ezugbe & Rathilal 2020).

Membrane fouling leads to performance degradation, alterations in membrane selectivity, and increased membrane separation resistance. These effects, in turn, impact the separation factor for target species in the feed, ultimately resulting in unstable product quality and reduced recovery (Li & Chen 2010). Several methods can be employed to mitigate fouling in

Table 7 | Pros and cons of different membrane technologies

Method	Pros	Cons	Used to treat
MF	Effectively remove particulate matter, versatile, energy efficient, simple to operate and maintain, wide range of pore sizes	Unable to remove small particles, membrane fouling, sometimes MF can be expensive (depends upon membrane and durability), complexity in changing parameters	Suspended solid, bacteria and microorganism, oil and grease, phosphorus, dyes and colors, cellulosic and fibrous materials iron and manganese
MBR	High treatment efficiency, reduced footprint, flexibility in design, enhanced nutrient removal, reduced sludge production, consistent treatment performances	High capital and operation costs, membrane fouling, energy intensive, complex operation and maintenance, chemical dependency, sensitive to shock loads	Organic compounds, biochemical oxygen demands, total suspended solid, nutrients pathogens, oil and grease, heavy metals, pharmaceutical and personal care products, dyes and colorants, and industrial effluents
RO	Highly effective filtration, versatility, compact design, selective removal, energy efficiency, reduced environmental impact	Low permeation flux, membrane fouling, inadequate selectivity, high capital and operation costs, waste generation, vulnerability to scaling	Salt and minerals, heavy metals, nitrates and nitrites, organic compounds, dissolved gases, microorganisms, PPCPs, dyes and colorants, radioactive substances, TDSs
Nanofiltration	Selective filtration, high flux rates, versatility, low energy consumption, cost-effective for certain applications	Limited salt rejection, membrane fouling, pressure sensitivity, variable membrane characteristics, complexity of operation	Hardness, dissolved salts, nitrates and nitrites, organic compounds, colorants and dyes, boron, pharmaceutical and personal care products, heavy metals, bacteria and microbes, TDSs
MD	Low operating temperature, suitable for brine concentration, versatility, potential for renewable energy integration, compact system design, reduced scaling issues	Energy intensive, membrane fouling, capital costs, complexity, limited scalability, product purity	Salt and minerals, volatile organic compounds, dissolved gases, pharmaceutical and personal care products, oil and grease, heavy metals, organic compound, colorants and dyes, nutrients, radioactive substances
PV	Energy efficiency, selective separation, operational flexibility, reduced environmental impact, no azeotropic limitation, continuous operation	Membrane degradation, membrane fouling, high capital costs, limited applicability, sensitive to feed composition, limited scalability	Organic compounds, azeotropic mixture, alcohol and esters, pharmaceutical and personal care products, volatile inorganic compounds, oil and grease, flavor and fragrant compounds, volatile acids and bases, and selective compounds removals
FO	Low energy consumption, suitable for high-salinity feed solutions, reduced fouling, potential for use in FO-driven processes, environmental sustainability, selective permeation	Draw solution challenges, limited desalination performance, membrane degradation, scaling issues, limited commercialization, complexity in system design	Salinity and TDSs, heavy metals, nutrients, dyes and colorants, organic compounds, radioactive ions, oil and grease, pathogens and microbes
LM	Selective extraction, versatility, potential for high efficiency, reduced scaling issues, operational flexibility	Membrane stability, limited selectivity, complexity in design, potential for emulsion issues, energy intensity, limited commercialization	Metal recovery, organic compound removal, acid and base recovery, color removal, oil and grease separation, pharmaceutical wastewater treatment, radioactive waste treatment, selective ion removal

membranes, including pre-filters, surface shearing, chemical agents, and adjustments to operational conditions. Additionally, techniques such as ultrasound, backflushing, membrane oscillation, chemical cleaning, pore structure optimization, and membrane surface modification offer effective options for fouling mitigation (Jepsen *et al.* 2018; Ullah *et al.* 2021). A novel electro-assisted membrane coupling technology has contributed to addressing this problem by repelling foulants such as charged natural organic matter, colloids, and bacteria from membrane surfaces in the presence of an electric field (Li *et al.* 2018b).

4. FUTURE CONSIDERATION AND CONCLUSION

As the global water crisis escalates, the search for effective and sustainable water purification technologies becomes increasingly crucial. Membrane technology, known for its efficiency and energy-conscious design, stands as a forefront solution to this challenge. Despite significant progress in water and wastewater treatment through material and module advancements, certain critical areas demand continuous attention. Fouling control and the pursuit of energy-efficient devices represent two key focal points for future exploration.

The persistent challenge of foulant accumulation on membranes requires innovative solutions. Research should focus on developing fouling-resistant membranes and exploring cost-effective pre-treatment techniques. A collaborative approach could yield breakthroughs in overcoming fouling, thereby enhancing the long-term efficiency of membrane systems. Energy efficiency remains an essential goal. Although the energy consumption of membrane processes has been significantly reduced, ongoing research is crucial to discovering novel ways to conserve energy in membrane-based water purification. Exploring hybrid techniques, such as the synergistic combination of forward-RO, holds immense promise. This hybrid approach, exemplified by its ability to eliminate high concentrations of phosphorus, ammonium, and salt from wastewater, signifies a leap toward resource-efficient water treatment.

As the research community refines these solutions, anchoring advancements in future economic viability and sustainability is essential. The application of cutting-edge technologies must align with practical constraints, emphasizing cost-effectiveness and environmental stewardship. Interdisciplinary collaboration and partnerships between researchers, engineers, policy-makers, and industry players will play a crucial role in shaping the trajectory of water purification innovation. In conclusion, the journey toward enhanced water purification is not merely a scientific pursuit but a collective commitment to securing a sustainable water future. Through ongoing research, innovation, and collaborative efforts, the promise of accessible, clean water for all remains within our reach.

ACKNOWLEDGEMENTS

The authors are thankful to the Department of Chemical Engineering, Chungbuk National University, and the Department of Chemical Science and Engineering, Kathmandu University (DUT) for their support. Assistant Professor Dr Midori Yasui (Kyoto University, Japan), and Assistant Professor Dr Devrim Kaya (San Diego State University, USA) for making comments on different version of manuscript draft.

AUTHOR CONTRIBUTIONS

S. R. K. conceptualized, drafted, edited, and commented on the manuscript. S. A. and R. S. drafted, edited, and commented on the manuscript. S. B., G. K., P. G., and N. T. edited and commented on the manuscript. A. T. drafted, structured, edited, and commented on the manuscript. G. J. structured and edited. All authors have read and approved the final manuscript.

FUNDING

This research received no external funding.

DATA AVAILABILITY STATEMENT

All relevant data are included in the paper or its Supplementary Information.

CONFLICT OF INTEREST

The authors declare there is no conflict.

REFERENCES

- Abdel-Fatah, M. A. 2018 Nanofiltration systems and applications in wastewater treatment. *Ain Shams Engineering Journal* **9** (4), 3077–3092.
- Aguiar, A., Andrade, L., Grossi, L., Pires, W. & Amaral, M. 2018 Acid mine drainage treatment by nanofiltration: A study of membrane fouling, chemical cleaning, and membrane ageing. *Separation and Purification Technology* **192**, 185–195.
- Ahmad, A., Waheed, S., Khan, S. M., e-Gul, S., Shafiq, M., Farooq, M., Sanaullah, K. & Jamil, T. 2015 Effect of silica on the properties of cellulose acetate/polyethylene glycol membranes for reverse osmosis. *Desalination* **355**, 1–10.
- Ahmed, S., Mofijur, M., Nuzhat, S., Chowdhury, A. T., Rafa, N., Uddin, M. A., Inayat, A., Mahlia, T. M. I., Ong, H. C., Chia, W. Y. & Show, P. L. 2021 Recent developments in physical, biological, chemical, and hybrid treatment techniques for removing emerging contaminants from wastewater. *Journal of Hazardous Materials* **416**, 125912.
- Alkhdhiri, A., Darwish, N. & Hilal, N. 2012 Membrane distillation: A comprehensive review. *Desalination* **287**, 2–18.
- Alsvik, I. L. & Hägg, M.-B. 2013 Pressure retarded osmosis and forward osmosis membranes: Materials and methods. *Polymers* **5** (1), 303–327.
- Alturki, A. A., McDonald, J. A., Khan, S. J., Price, W. E., Nghiem, L. D. & Elimelech, M. 2013 Removal of trace organic contaminants by the forward osmosis process. *Separation and Purification Technology* **103**, 258–266.
- Aptel, P., Challard, N., Cuny, J. & Neel, J. 1976 Application of the pervaporation process to separate azeotropic mixtures. *Journal of Membrane Science* **1**, 271–287.
- Arcanjo, G. S., Ricci, B. C., Dos Santos, C. R., Costa, F. C. R., Silva, U. C. M., Munteer, A. H., Koch, K., Da Silva, P. R., Santos, V. L. & Amaral, M. C. S. 2021 Effective removal of pharmaceutical compounds and estrogenic activity by a hybrid anaerobic osmotic membrane bioreactor–membrane distillation system treating municipal sewage. *Chemical Engineering Journal* **416**, 129151.
- Asempour, F., Emadzadeh, D., Matsuura, T. & Kruczek, B. 2018 Synthesis and characterization of novel cellulose nanocrystals-based thin film nanocomposite membranes for reverse osmosis applications. *Desalination* **439**, 179–187.
- A Shirazi, M. M. & Kargari, A. 2015 A review on applications of membrane distillation (MD) process for wastewater treatment. *Journal of Membrane Science and Research* **1** (3), 101–112.
- Babaei, F., Ehrampoush, M. H., Eslami, H., Ghaneian, M. T., Fallahzadeh, H., Talebi, P., Fard, R. F. & Ebrahimi, A. A. 2019 Removal of linear alkylbenzene sulfonate and turbidity from greywater by a hybrid multi-layer slow sand filter microfiltration ultrafiltration system. *Journal of Cleaner Production* **211**, 922–931.
- Baker, R. W. 2012 *Membrane Technology and Applications*. John Wiley & Sons, Hoboken, NJ, USA.
- Bhattacharya, S., Saha, I., Mukhopadhyay, A., Chattopadhyay, D., Ghosh, U. C. & Chatterjee, D. 2013 Role of nanotechnology in water treatment and purification: Potential applications and implications. *International Journal of Chemical Science and Technology* **3** (3), 59.
- Bell, E. A., Poynor, T. E., Newhart, K. B., Regnery, J., Coday, B. D. & Cath, T. Y. 2017 Produced water treatment using forward osmosis membranes: Evaluation of extended-time performance and fouling. *Journal of Membrane Science* **525**, 77–88.
- Bera, S. P., Godhaniya, M. & Kothari, C. 2022 Emerging and advanced membrane technology for wastewater treatment: A review. *Journal of Basic Microbiology* **62** (3–4), 245–259.
- Blandin, G., Ferrari, F., Lesage, G., Le-Clech, P., Héran, M. & Martinez-Lladó, X. 2020 Forward osmosis as concentration process: Review of opportunities and challenges. *Membranes* **10** (10), 284.
- Butterworth, R. F. 2010 Metal toxicity, liver disease and neurodegeneration. *Neurotoxicity Research* **18**, 100–105.
- Cao, X., Wang, K. & Feng, X. 2021 Removal of phenolic contaminants from water by pervaporation. *Journal of Membrane Science* **623**, 119043.
- Cath, T. Y., Childress, A. E. & Elimelech, M. 2006 Forward osmosis: Principles, applications, and recent developments. *Journal of Membrane Science* **281** (1–2), 70–87.
- Chimuka, L., Cukrowska, E. & Jönsson, J. Å. 2004 Why liquid membrane extraction is an attractive alternative in sample preparation. *Pure and Applied Chemistry* **76** (4), 707–722.
- Coday, B. D., Almaraz, N. & Cath, T. Y. 2015 Forward osmosis desalination of oil and gas wastewater: Impacts of membrane selection and operating conditions on process performance. *Journal of Membrane Science* **488**, 40–55.
- Curcio, E. & Drioli, E. 2005 Membrane distillation and related operations – A review. *Separation and Purification Reviews* **34** (1), 35–86.
- Dai, Y., Zhang, N., Xing, C., Cui, Q. & Sun, Q. 2019 The adsorption, regeneration and engineering applications of biochar for removal organic pollutants: A review. *Chemosphere* **223**, 12–27.
- De Bruijn, F., Sun, L., Olujić, Ž., Jansens, P. J. & Kapteijn, F. 2003 Influence of the support layer on the flux limitation in pervaporation. *Journal of Membrane Science* **223** (1–2), 141–156.
- De Wever, H., Weiss, S., Reemtsma, T., Vereecken, J., Müller, J., Knepper, T., Rörden, O., Gonzalez, S., Barcelo, D. & Dolores Hernando, M. 2007 Comparison of sulfonated and other micropollutants removal in membrane bioreactor and conventional wastewater treatment. *Water Research* **41** (4), 935–945.
- Drioli, E., Ali, A. & Macedonio, F. 2015 Membrane distillation: Recent developments and perspectives. *Desalination* **356**, 56–84.
- Isnasyauqiah, Elma, M., Pradana, E. A., Ul-haq, M. D., Rampun, E. L. A., Rahma, A., Harivram, A. S. K., Assyaifi, Z. L. & Kamelia, Y. 2022 Hollow fiber membrane applied for Sasirangan wastewater desalination integrated with photocatalysis and pervaporation set-up. *Materials Today: Proceedings* **51**, 1298–1302.

- Fan, S., Xiao, Z., Li, M. & Li, S. 2017 Ethanol fermentation coupled with pervaporation by energy efficient mechanical vapor compression. *Energy Procedia* **105**, 933–938.
- Farahbakhsh, K., Svrcek, C., Guest, R. K. & Smith, D. W. 2004 A review of the impact of chemical pretreatment on low-pressure water treatment membranes. *Journal of Environmental Engineering and Science* **3** (4), 237–253.
- Fu, C., Cai, D., Hu, S., Miao, Q., Wang, Y., Qin, P., Wang, Z. & Tan, T. 2016 Ethanol fermentation integrated with PDMS composite membrane: An effective process. *Bioresource Technology* **200**, 648–657.
- Fujioka, T., Khan, S. J., McDonald, J. A. & Nghiem, L. D. 2015 Rejection of trace organic chemicals by a hollow fibre cellulose triacetate reverse osmosis membrane. *Desalination* **368**, 69–75.
- Gan, G., Fan, S., Li, X., Zhang, Z. & Hao, Z. 2023 Adsorption and membrane separation for removal and recovery of volatile organic compounds. *Journal of Environmental Sciences* **123**, 96–115.
- García-Rodríguez, A., Matamoros, V., Fontàs, C. & Salvadó, V. 2014 The ability of biologically based wastewater treatment systems to remove emerging organic contaminants – A review. *Environmental Science and Pollution Research* **21**, 11708–11728.
- Gaur, N., Narasimhulu, K. & PydiSetty, Y. 2018 Recent advances in the bio-remediation of persistent organic pollutants and its effect on environment. *Journal of Cleaner Production* **198**, 1602–1631.
- Ge, Q., Ling, M. & Chung, T.-S. 2013 Draw solutions for forward osmosis processes: Developments, challenges, and prospects for the future. *Journal of Membrane Science* **442**, 225–237.
- Ghaseminezhad, S. M., Barikani, M. & Salehirad, M. 2019 Development of graphene oxide-cellulose acetate nanocomposite reverse osmosis membrane for seawater desalination. *Composites Part B: Engineering* **161**, 320–327.
- González, S., Petrovic, M. & Barceló, D. 2007 Removal of a broad range of surfactants from municipal wastewater—comparison between membrane bioreactor and conventional activated sludge treatment. *Chemosphere* **67** (2), 335–345.
- Goswami, L., Vinoth Kumar, R., Borah, S. N., Arul Manikandan, N., Pakshirajan, K. & Pugazhenthii, G. 2018 Membrane bioreactor and integrated membrane bioreactor systems for micropollutant removal from wastewater: A review. *Journal of Water Process Engineering* **26**, 314–328.
- Goswami, L., Kumar, R. V., Pakshirajan, K. & Pugazhenthii, G. 2019 A novel integrated biodegradation – microfiltration system for sustainable wastewater treatment and energy recovery. *Journal of Hazardous Materials* **365**, 707–715.
- Green, D. & Southard, M. (eds) 2019 Section 9—Process economics. In: *Perry's Chemical Engineers' Handbook*, 7th edn. McGraw-Hill Education, New York, NY, USA, pp. 9–53.
- Gul, A., Hruza, J. & Yalcinkaya, F. 2021 Fouling and chemical cleaning of microfiltration membranes: A mini-review. *Polymers* **13** (6), 846.
- Guo, W., Pan, B., Sakkiah, S., Yavas, G., Ge, W., Zou, W., Tong, W. & Hong, H. 2019 Persistent organic pollutants in food: Contamination sources, health effects and detection methods. *International Journal of Environmental Research and Public Health* **16** (22), 4361.
- Hailemariam, R. H., Woo, Y. C., Damtie, M. M., Kim, B. C., Park, K.-D. & Choi, J.-S. 2020 Reverse osmosis membrane fabrication and modification technologies and future trends: A review. *Advances in Colloid and Interface Science* **276**, 102100.
- Han, L., Tan, Y. Z., Netke, T., Fane, A. G. & Chew, J. W. 2017 Understanding oily wastewater treatment via membrane distillation. *Journal of Membrane Science* **539**, 284–294.
- Hanafi, M. F. & Sapawe, N. 2020 A review on the current techniques and technologies of organic pollutants removal from water/wastewater. *Materials Today: Proceedings* **31** (1), A158–A165. doi:10.1016/j.matpr.2021.01.265.
- Ho, D., Vigneswaran, S. & Ngo, H. 2010 Integration of photocatalysis and microfiltration in removing effluent organic matter from treated sewage effluent. *Separation Science and Technology* **45** (2), 155–162.
- Howe, K. J., Hand, D. W., Crittenden, J. C., Trussell, R. R. & Tchobanoglous, G. 2012 *Principles of Water Treatment*. John Wiley & Sons, Hoboken, NJ, USA.
- Huang, H., Schwab, K. & Jacangelo, J. G. 2009 Pretreatment for low pressure membranes in water treatment: A review. *Environmental Science & Technology* **43** (9), 3011–3019.
- Jacangelo, J. G., Trussell, R. R. & Watson, M. 1997 Role of membrane technology in drinking water treatment in the United States. *Desalination* **113** (2–3), 119–127.
- Jamil, S., Jeong, S. & Vigneswaran, S. 2016 Application of pressure assisted forward osmosis for water purification and reuse of reverse osmosis concentrate from a water reclamation plant. *Separation and Purification Technology* **171**, 182–190.
- Jefferson, B., Laine, A. L., Judd, S. J. & Stephenson, T. 2000 Membrane bioreactors and their role in wastewater reuse. *Water Science and Technology* **41** (1), 197–204.
- Jepsen, K. L., Bram, M. V., Pedersen, S. & Yang, Z. 2018 Membrane fouling for produced water treatment: A review study from a process control perspective. *Water* **10** (7), 847.
- Jin, X., Shan, J., Wang, C., Wei, J. & Tang, C. Y. 2012 Rejection of pharmaceuticals by forward osmosis membranes. *Journal of Hazardous Materials* **227**, 55–61.
- Juang, Y., Nurhayati, E., Huang, C., Pan, J. R. & Huang, S. 2013 A hybrid electrochemical advanced oxidation/microfiltration system using BDD/Ti anode for acid yellow 36 dye wastewater treatment. *Separation and Purification Technology* **120**, 289–295.
- Juholin, P., Kääriäinen, M.-L., Riihimäki, M., Sliz, R., Aguirre, J. L., Pirlä, M., Fabritius, T., Cameron, D. & Keiski, R. L. 2018 Comparison of ALD coated nanofiltration membranes to unmodified commercial membranes in mine wastewater treatment. *Separation and Purification Technology* **192**, 69–77.

- Kavaiya, A. R. & Raval, H. D. 2022 Highly selective and antifouling reverse osmosis membrane by crosslinkers induced surface modification. *Environmental Technology* **43** (14), 2155–2166.
- Kazemi, P., Peydayesh, M., Bandegi, A., Mohammadi, T. & Bakhtiari, O. 2014 Stability and extraction study of phenolic wastewater treatment by supported liquid membrane using tributyl phosphate and sesame oil as liquid membrane. *Chemical Engineering Research and Design* **92** (2), 375–383.
- Khan, F. I. & Ghoshal, A. K. 2000 Removal of volatile organic compounds from polluted air. *Journal of Loss Prevention in the Process Industries* **13** (6), 527–545.
- Kyburz, M., Meindersma, G. W. & Bargeman, G. 2021 Nanofiltration in the chemical processing industry. *Nanofiltration: Principles, Applications, and New Materials* **2**, 543–597.
- Le-Clech, P., Chen, V. & Fane, T. A. 2006 Fouling in membrane bioreactors used in wastewater treatment. *Journal of Membrane Science* **284** (1–2), 17–53.
- Lee, A., Elam, J. W. & Darling, S. B. 2016 Membrane materials for water purification: Design, development, and application. *Environmental Science: Water Research & Technology* **2** (1), 17–42.
- Li, N. N. 1968 Separating hydrocarbons with liquid membranes. Google Patents.
- Li, N. N. 1978 Facilitated transport through liquid membranes. *Journal of Membrane Science* **3** (2), 265–269.
- Li, J.-L. & Chen, B.-H. 2005 Review of CO₂ absorption using chemical solvents in hollow fiber membrane contactors. *Separation and Purification Technology* **41** (2), 109–122.
- Li, H. & Chen, V. 2010 Membrane fouling and cleaning in food and bioprocessing. In: *Membrane Technology* (Cui, Z. F. & Muralidhara, H. S. (eds)). Elsevier, Amsterdam, Netherlands, pp. 213–254.
- Li, L. & Visvanathan, C. 2017 Membrane technology for surface water treatment: Advancement from microfiltration to membrane bioreactor. *Reviews in Environmental Science and Bio/Technology* **16**, 737–760.
- Li, D., Yao, J., Sun, H., Liu, B., Li, D., Van Agtmaal, S. & Feng, C. 2018a Preparation and characterization of SiO₂/PDMS/PVDF composite membrane for phenols recovery from coal gasification wastewater in pervaporation. *Chemical Engineering Research and Design* **132**, 424–435.
- Li, C., Guo, X., Wang, X., Fan, S., Zhou, Q., Shao, H., Hu, W., Li, C., Tong, L. & Kumar, R. R. 2018b Membrane fouling mitigation by coupling applied electric field in membrane system: Configuration, mechanism and performance. *Electrochimica Acta* **287**, 124–134.
- Li, C., Deng, W., Gao, C., Xiang, X., Feng, X., Batchelor, B. & Li, Y. 2019 Membrane distillation coupled with a novel two-stage pretreatment process for petrochemical wastewater treatment and reuse. *Separation and Purification Technology* **224**, 23–32.
- Li, C., Feng, G., Pan, Z., Song, C., Fan, X., Tao, P., Wang, T., Shao, M. & Zhao, S. 2020 High-performance electrocatalytic microfiltration CuO/Carbon membrane by facile dynamic electrodeposition for small-sized organic pollutants removal. *Journal of Membrane Science* **601**, 117913.
- Li, Y., Huo, B., Xu, Z., Qi, H., Li, X., Cui, P., Zhu, Z., Wang, Y., Yang, J. & Gao, J. 2022 Energy-saving and environmentally friendly pervaporation-distillation hybrid process for alcohol and ester recovery from wastewater containing three binary azeotropes. *Separation and Purification Technology* **281**, 119889.
- Liao, Y., Zheng, G., Huang, J. J., Tian, M. & Wang, R. 2020 Development of robust and superhydrophobic membranes to mitigate membrane scaling and fouling in membrane distillation. *Journal of Membrane Science* **601**, 117962.
- Lim, S. K., Goh, K., Bae, T.-H. & Wang, R. 2017 Polymer-based membranes for solvent-resistant nanofiltration: A review. *Chinese Journal of Chemical Engineering* **25** (11), 1653–1675.
- Lin, H., Gao, W., Meng, F., Liao, B.-Q., Leung, K.-T., Zhao, L., Chen, J. & Hong, H. 2012 Membrane bioreactors for industrial wastewater treatment: A critical review. *Critical Reviews in Environmental Science and Technology* **42** (7), 677–740.
- Liu, P., Zhang, H., Feng, Y., Shen, C. & Yang, F. 2015 Integrating electrochemical oxidation into forward osmosis process for removal of trace antibiotics in wastewater. *Journal of Hazardous Materials* **296**, 248–255.
- Liu, L., Xie, X., Qi, S., Li, R., Zhang, X., Song, X. & Gao, C. 2019 Thin film nanocomposite reverse osmosis membrane incorporated with UiO-66 nanoparticles for enhanced boron removal. *Journal of Membrane Science* **580**, 101–109.
- Liu, C., Dong, G., Tsuru, T. & Matsuyama, H. 2021a Organic solvent reverse osmosis membranes for organic liquid mixture separation: A review. *Journal of Membrane Science* **620**, 118882.
- Liu, C., Takagi, R., Saeki, D., Cheng, L., Shintani, T., Yasui, T. & Matsuyama, H. 2021b Highly improved organic solvent reverse osmosis (OSRO) membrane for organic liquid mixture separation by simple heat treatment. *Journal of Membrane Science* **618**, 118710.
- Liu, Y., Liu, H. & Shen, Z. 2021c Nanocellulose based filtration membrane in industrial waste water treatment: A review. *Materials* **14** (18), 5398.
- Luan, J. & Plaisier, A. 2004 Study on treatment of wastewater containing nitrophenol compounds by liquid membrane process. *Journal of Membrane Science* **229** (1–2), 235–239.
- Luo, W., Phan, H. V., Li, G., Hai, F. I., Price, W. E., Elimelech, M. & Nghiem, L. D. 2017 An osmotic membrane bioreactor–membrane distillation system for simultaneous wastewater reuse and seawater desalination: Performance and implications. *Environmental Science & Technology* **51** (24), 14311–14320.
- Madsen, H. T., Bajraktari, N., Hélix-Nielsen, C., Van Der Bruggen, B. & Søgaard, E. G. 2015 Use of biomimetic forward osmosis membrane for trace organics removal. *Journal of Membrane Science* **476**, 469–474.

- Malkoske, T. A., Bérubé, P. R. & Andrews, R. C. 2020 Coagulation/flocculation prior to low pressure membranes in drinking water treatment: A review. *Environmental Science: Water Research & Technology* **6** (11), 2993–3023.
- Mameda, N., Park, H., Shah, S. S. A., Lee, K., Li, C.-W., Naddeo, V. & Choo, K.-H. 2020 Highly robust and efficient Ti-based Sb-SnO₂ anode with a mixed carbon and nitrogen interlayer for electrochemical 1, 4-dioxane removal from water. *Chemical Engineering Journal* **393**, 124794.
- Marchetti, P., Jimenez Solomon, M. F., Szekely, G. & Livingston, A. G. 2014 Molecular separation with organic solvent nanofiltration: A critical review. *Chemical Reviews* **114** (21), 10735–10806.
- Melliti, E., Touati, K., Abidi, H. & Elfil, H. 2019 Iron fouling prevention and membrane cleaning during reverse osmosis process. *International Journal of Environmental Science and Technology* **16** (7), 3809–3818.
- Mohammad, A. W., Teow, Y. H., Ang, W. L., Chung, Y. T., Oatley-Radcliffe, D. L. & Hilal, N. 2015 Nanofiltration membranes review: Recent advances and future prospects. *Desalination* **356**, 226–254.
- Mulyanti, R. & Susanto, H. 2018 Wastewater treatment by nanofiltration membranes. In *IOP Conference Series: Earth and Environmental Science*. IOP Publishing, Bristol, UK.
- Nath, K. 2017 *Membrane Separation Processes*. PHI Learning Pvt. Ltd, Delhi, India.
- Nath, K., Dave, H. K. & Patel, T. M. 2018 Revisiting the recent applications of nanofiltration in food processing industries: Progress and prognosis. *Trends in Food Science & Technology* **73**, 12–24.
- Nie, L., Chuah, C. Y., Bae, T. & Lee, J. 2021 Graphene-based advanced membrane applications in organic solvent nanofiltration. *Advanced Functional Materials* **31** (6), 2006949.
- Noble, R. D. & Way, J. D. 1987 *Liquid Membranes: Theory and Applications*. American Chemical Society, Washington, DC, USA.
- Nqombolo, A., Mpupa, A., Moutloali, R. M. & Nomngongo, P. N. 2018 Wastewater treatment using membrane technology. *Wastewater and Water Quality* **29**, 30–40.
- Obotey Ezugbe, E. & Rathilal, S. 2020 Membrane technologies in wastewater treatment: A review. *Membranes* **10** (5), 89.
- Onsekizoglu, P. 2012 Membrane distillation: Principle, advances, limitations and future prospects in food industry. In: Zereszki, S. (ed.) *Distillation – Advances from Modeling to Applications*. InTech, p. 282.
- Othman, N., Zailani, S. & Mili, N. 2011 Recovery of synthetic dye from simulated wastewater using emulsion liquid membrane process containing tri-dodecyl amine as a mobile carrier. *Journal of Hazardous Materials* **198**, 103–112.
- Ouyang, W., Chen, T., Shi, Y., Tong, L., Chen, Y., Wang, W., Yang, J. & Xue, J. 2019 Physico-chemical processes. *Water Environment Research* **91** (10), 1350–1377.
- Park, S.-H., Kwon, S. J., Shin, M. G., Park, M. S., Lee, J. S., Park, C. H., Park, H. & Lee, J.-H. 2018 Polyethylene-supported high performance reverse osmosis membranes with enhanced mechanical and chemical durability. *Desalination* **436**, 28–38.
- Qu, F., Yang, Z., Li, X., Yu, H., Pan, Z., Fan, G., He, J. & Rong, H. 2021 Membrane fouling control by UV/persulfate in tertiary wastewater treatment with ultrafiltration: A comparison with UV/hydroperoxide and role of free radicals. *Separation and Purification Technology* **257**, 117877.
- Quist-Jensen, C. A., Macedonio, F. & Drioli, E. 2015 Membrane technology for water production in agriculture: Desalination and wastewater reuse. *Desalination* **364**, 17–32.
- Ramos, R. L., Martins, M. F., Lebron, Y. A. R., Moreira, V. R., Reis, B. G., Grossi, L. B. & Amaral, M. C. S. 2021 Membrane distillation process for phenolic compounds removal from surface water. *Journal of Environmental Chemical Engineering* **9** (4), 105588.
- Reis, M. T. A., De Freitas, O. M. F., Ismael, M. R. C. & Carvalho, J. M. R. 2007 Recovery of phenol from aqueous solutions using liquid membranes with Cyanex 923. *Journal of Membrane Science* **305** (1–2), 313–324.
- Ren, J., Li, J., Chen, Z. & Cheng, F. 2018 Fate and wetting potential of bio-refractory organics in membrane distillation for coke wastewater treatment. *Chemosphere* **208**, 450–459.
- Ren, Y., Yu, F., Li, X.-G. & Ma, J. 2021 Recent progress on adsorption and membrane separation for organic contaminants on multi-dimensional graphene. *Materials Today Chemistry* **22**, 100603.
- Rezazakemi, M., Marjani, A. & Shirazian, S. 2018 Organic solvent removal by pervaporation membrane technology: Experimental and simulation. *Environmental Science and Pollution Research* **25** (20), 19818–19825.
- Riley, S. M., Oliveira, J. M. S., Regnery, J. & Cath, T. Y. 2016 Hybrid membrane bio-systems for sustainable treatment of oil and gas produced water and fracturing flowback water. *Separation and Purification Technology* **171**, 297–311.
- Rout, P. R., Zhang, T. C., Bhunia, P. & Surampalli, R. Y. 2021 Treatment technologies for emerging contaminants in wastewater treatment plants: A review. *Science of the Total Environment* **753**, 141990.
- Said, I. A., Chomiak, T. R., He, Z. & Li, Q. 2020 Low-cost high-efficiency solar membrane distillation for treatment of oil produced waters. *Separation and Purification Technology* **250**, 117170.
- San Román, M., Bringas, E., Ibañez, R. & Ortiz, I. 2010 Liquid membrane technology: Fundamentals and review of its applications. *Journal of Chemical Technology & Biotechnology* **85** (1), 2–10.
- Sardari, K., Fyfe, P. & Wickramasinghe, S. R. 2019 Integrated electrocoagulation – forward osmosis – membrane distillation for sustainable water recovery from hydraulic fracturing produced water. *Journal of Membrane Science* **574**, 325–337.
- Sauchelli, M., Pellegrino, G., D'Haese, A., Rodríguez-Roda, I. & Gernjak, W. 2018 Transport of trace organic compounds through novel forward osmosis membranes: Role of membrane properties and the draw solution. *Water Research* **141**, 65–73.
- Seah, M. Q., Lau, W. J., Goh, P. S., Tseng, H.-H., Wahab, R. A. & Ismail, A. F. 2020 Progress of interfacial polymerization techniques for polyamide thin film (nano) composite membrane fabrication: A comprehensive review. *Polymers* **12** (12), 2817.

- Sekulić, J., ten Elshof, J. E. & Blank, D. H. 2005 Separation mechanism in dehydration of water/organic binary liquids by pervaporation through microporous silica. *Journal of Membrane Science* **254** (1–2), 267–274.
- Shahid, M. K., Kashif, A., Fuwad, A. & Choi, Y. 2021 Current advances in treatment technologies for removal of emerging contaminants from water – A critical review. *Coordination Chemistry Reviews* **442**, 213993.
- Shin, M. G., Park, S.-H., Kwon, S. J., Kwon, H.-E., Park, J. B. & Lee, J.-H. 2019 Facile performance enhancement of reverse osmosis membranes via solvent activation with benzyl alcohol. *Journal of Membrane Science* **578**, 220–229.
- Shin, Y.-U., Yun, E.-T., Kim, J., Lee, H., Hong, S. & Lee, J. 2020 Electrochemical oxidation–membrane distillation hybrid process: Utilizing electric resistance heating for distillation and membrane defouling through thermal activation of anodically formed persulfate. *Environmental Science & Technology* **54** (3), 1867–1877.
- Shon, H., Vigneswaran, S. & Kandasamy, J. 2002 *Membrane Technology for Organic Removal in Wastewater*. Encyclopedia of Life Support Systems (EOLSS).
- Shon, H., Phuntsho, S., Chaudhary, D. S., Vigneswaran, S. & Cho, J. 2013 Nanofiltration for water and wastewater treatment – A mini review. *Drinking Water Engineering and Science* **6** (1), 47–53.
- Singh, R. & Hankins, N. 2016 *Emerging Membrane Technology for Sustainable Water Treatment*. Elsevier, Amsterdam, Netherlands.
- Singh, R. & Purkait, M. K. 2019 Microfiltration membranes. In: *Membrane Separation Principles and Applications*. Elsevier, Amsterdam, Netherlands, pp. 111–146.
- Sonawane, S., Thakur, P., Sonawane, S. H. & Bhanvase, B. A. 2021 Nanomaterials for membrane synthesis: Introduction, mechanism, and challenges for wastewater treatment. In: *Handbook of Nanomaterials for Wastewater Treatment*. Elsevier, Amsterdam, Netherlands, pp. 537–553.
- Song, X., Luo, W., McDonald, J., Khan, S. J., Hai, F. I., Price, W. E. & Nghiem, L. D. 2018 An anaerobic membrane bioreactor–membrane distillation hybrid system for energy recovery and water reuse: Removal performance of organic carbon, nutrients, and trace organic contaminants. *Science of the Total Environment* **628**, 358–365.
- Subramaniam, M. N., Goh, P.-S., Lau, W.-J., Ng, B.-C. & Ismail, A. F. 2019 Development of nanomaterial-based photocatalytic membrane for organic pollutants removal. In: *Advanced Nanomaterials for Membrane Synthesis and Its Applications*. Elsevier, Amsterdam, Netherlands, pp. 45–67.
- Sun, J., Liu, S., Kang, J., Chen, Z., Cai, L., Guo, Y., Shen, J. & Wang, Z. 2021 Fabrication of cementitious microfiltration membrane and its catalytic ozonation for the removal of small molecule organic pollutants. *Membranes* **11** (7), 532.
- Tadkaew, N., Sivakumar, M., Khan, S. J., McDonald, J. A. & Nghiem, L. D. 2010 Effect of mixed liquor pH on the removal of trace organic contaminants in a membrane bioreactor. *Bioresource Technology* **101** (5), 1494–1500.
- Tavangar, T., Jalali, K., Alaei Shahmirzadi, M. A. & Karimi, M. 2019 Toward real textile wastewater treatment: Membrane fouling control and effective fractionation of dyes/inorganic salts using a hybrid electrocoagulation–nanofiltration process. *Separation and Purification Technology* **216**, 115–125.
- Toth, A. J., Haaz, E., Nagy, T., Tarjani, A.J., Fozer, D., Andre, A., Valentinyi, N., Solti, S. & Mizsey, P. 2018 Treatment of pharmaceutical process wastewater with hybrid separation method: Distillation and hydrophilic pervaporation. *Waste Treatment and Recovery* **3** (1), 8–13.
- Ullah, A., Tanudjaja, H. J., Ouda, M., Hasan, S. W. & Chew, J. W. 2021 Membrane fouling mitigation techniques for oily wastewater: A short review. *Journal of Water Process Engineering* **43**, 102293.
- Urase, T., Kagawa, C. & Kikuta, T. 2005 Factors affecting removal of pharmaceutical substances and estrogens in membrane separation bioreactors. *Desalination* **178** (1–3), 107–113.
- Urošević, T. & Trivunac, K. 2020 Achievements in low-pressure membrane processes microfiltration (MF) and ultrafiltration (UF) for wastewater and water treatment. In: *Current Trends and Future Developments on (Bio-) Membranes*. Elsevier, Amsterdam, Netherlands, pp. 67–107.
- Van der Merwe, I. 1998 Application of nanofiltration in metal recovery. *Journal of the Southern African Institute of Mining and Metallurgy* **98** (7), 339–341.
- Van Dijk, L. & Roncken, G. 1997 Membrane bioreactors for wastewater treatment: The state of the art and new developments. *Water Science and Technology* **35** (10), 35–41.
- van't Oever, R. 2005 MBR focus: Is submerged best? *Filtration & Separation* **42** (5), 24–27.
- Voicu, S. & Thakur, V. 2021 Graphene-based composite membranes for nanofiltration: Performances and future perspectives. *Emergent Materials* **5**, 1429–1441.
- Wang, Y., Mei, X., Ma, T., Xue, C., Wu, M., Ji, M. & Li, Y. 2018 Green recovery of hazardous acetonitrile from high-salt chemical wastewater by pervaporation. *Journal of Cleaner Production* **197**, 742–749.
- Wang, H., Li, C., Xu, Q., Liu, C., Zhang, Z., Du, X., Hao, X. & Guan, G. 2021a Mass transport and pervaporation recovery of aniline with high-purity from dilute aqueous solution by PEBA/PVDF composite membranes. *Separation and Purification Technology* **268**, 118708.
- Wang, Z., Qin, Y., Xu, X., Sun, J., Shen, J., Ning, X. & Li, N. 2021b Laminated graphene oxide membrane for recovery of mercury-containing wastewater by pervaporation. *Applied Water Science* **11** (7), 1–10.
- Warsinger, D. M., Chakraborty, S., Tow, E. W., Plumlee, M. H., Bellona, C., Loutatidou, S., Karimi, L., Mikelonis, A. M., Achilli, A. & Ghassemi, A. 2018 A review of polymeric membranes and processes for potable water reuse. *Progress in Polymer Science* **81**, 209–237.
- Weerasekara, N. A., Choo, K.-H. & Lee, C.-H. 2016 Biofouling control: Bacterial quorum quenching versus chlorination in membrane bioreactors. *Water Research* **103**, 293–301.

- Wenten, I. G. 2016 Reverse osmosis applications: Prospect and challenges. *Desalination* **391**, 112–125.
- Wijekoon, K. C., Hai, F. I., Kang, J., Price, W. E., Cath, T. Y. & Nghiem, L. D. 2014 Rejection and fate of trace organic compounds (TrOCs) during membrane distillation. *Journal of Membrane Science* **453**, 636–642.
- Wolf, K., Yazdani, A. & Yates, P. 1991 Chlorinated solvents: Will the alternatives be safer? *Journal of the Air & Waste Management Association* **41** (8), 1055–1061.
- Xie, M., Nghiem, L. D., Price, W. E. & Elimelech, M. 2013 A forward osmosis–membrane distillation hybrid process for direct sewer mining: System performance and limitations. *Environmental Science & Technology* **47** (23), 13486–13493.
- Yadav, S., Ibrar, I., Bakly, S., Khanafer, D., Altaee, A., Padmanaban, V. C., Samal, A. K. & Hawari, A. H. 2020 Organic fouling in forward osmosis: A comprehensive review. *Water* **12** (5), 1505.
- Yang, F. & Yang, P. 2022 Biopolymer-based membrane adsorber for removing contaminants from aqueous solution: Progress and prospects. *Macromolecular Rapid Communications* **43** (3), 2100669.
- Yang, Z., Zhou, Y., Feng, Z., Rui, X., Zhang, T. & Zhang, Z. 2019 A review on reverse osmosis and nanofiltration membranes for water purification. *Polymers* **11** (8), 1252.
- Yao, L., Qin, Z., Chen, Q., Zhao, M., Zhao, H., Ahmad, W., Fan, L. & Zhao, L. 2018 Insights into the nanofiltration separation mechanism of monosaccharides by molecular dynamics simulation. *Separation and Purification Technology* **205**, 48–57.
- Yao, M., Duan, L., Song, Y. & Hermanowicz, S. W. 2021 Degradation mechanism of Ibuprofen via a forward osmosis membrane bioreactor. *Bioresource Technology* **321**, 124448.
- Zhang, X., Ning, Z., Wang, D. K. & Diniz Da Costa, J. C. 2014 Processing municipal wastewaters by forward osmosis using CTA membrane. *Journal of Membrane Science* **468**, 269–275.
- Zhang, Y., Zhao, P., Li, J., Hou, D., Wang, J. & Liu, H. 2016 A hybrid process combining homogeneous catalytic ozonation and membrane distillation for wastewater treatment. *Chemosphere* **160**, 134–140.
- Zhang, H., Wang, S., Tang, J., Li, N., Li, Y., Cui, P., Wang, Y., Zheng, S., Zhu, Z. & Ma, Y. 2021 Multi-objective optimization and control strategy for extractive distillation with dividing-wall column/pervaporation for separation of ternary azeotropes based on mechanism analysis. *Energy* **229**, 120774.
- Zhao, G., Zou, J., Chen, X., Zhang, T., Yu, J., Zhou, S., Li, C. & Jiao, F. 2020 Integration of microfiltration and visible-light-driven photocatalysis on a ZnWO₄ nanoparticle/nickel–aluminum-layered double hydroxide membrane for enhanced water purification. *Industrial & Engineering Chemistry Research* **59** (14), 6479–6487.
- Zhu, S., Li, M. & El-Din, M. G. 2018 The roles of pH and draw solute on forward osmosis process treating aqueous naphthenic acids. *Journal of Membrane Science* **549**, 456–465.
- Zou, Q., Zhang, Z., Li, H., Pei, W., Ding, M., Xie, Z., Huo, Y. & Li, H. 2020 Synergistic removal of organic pollutant and metal ions in photocatalysis-membrane distillation system. *Applied Catalysis B: Environmental* **264**, 118463.

First received 30 September 2023; accepted in revised form 11 March 2024. Available online 10 April 2024