

# Exploring the Impact of the Presence of 9,9'-Spirobifluorene Moieties on the Performance of Carbonyl-Based Multiresonant Thermally Activated Delayed Fluorescence Organic Light-Emitting Diodes

Janine Haug, Sen Wu, Hassan Hafeez, Maximilian Schustek, Mahni Fatahi, Yannik T. Woordes, Martin Nieger, Olaf Fuhr, Burkhard Luy, Ifor D.W. Samuel,\* Stefan Bräse,\* and Eli Zysman-Colman\*

The impact of the decoration of the multiresonant thermally activated delayed fluorescence (MR-TADF) core DiKTa with 9,9'-spirobifluorene (SBF) groups is investigated with respect to the impact of number, position, and incorporation-type of the SBF unit on the photophysical and optoelectronic properties. This approach allows for the development of narrowband, high-efficiency organic light emitting diodes (OLEDs) with moderate efficiency roll-off. The MR-TADF emitters DiKTaSBF, 3-SBF-DiKTa, 7-SBF-DiKTa, and 7-SBF-DiKTaSBF, differ in the number, position, and incorporation-type of the SBF unit. Sky-blue OLEDs with DiKTaSBF and 3-SBF-DiKTa show superior performance with maximal external quantum efficiencies ( $EQE_{max}$ ) of 26.1 and 27.0%, respectively, while all four families of OLEDs show a moderate efficiency roll-off. Narrowband emissions with full-width at half maximum (FWHM) of 32 and 35 nm are observed for 7-modified emitters, whereas for the devices with emitters containing SBF groups at the 3-position show a broadened emission, with FWHM of  $\approx 50$  nm. These findings highlight the effect of the regiochemistry of the SBF group on the optoelectronic properties and the corresponding impact on the performance of the OLEDs.

## 1. Introduction

Multiresonant thermally activated delayed fluorescence (MR-TADF) compounds introduced by Hatakeyama et al.<sup>[1]</sup> have emerged as a promising class of emitters for use in organic light-emitting diodes (OLEDs). This is because unlike donor-acceptor TADF emitters, MR-TADF compounds show bright and narrowband emission, and therefore, the OLEDs emit with high color purity and high external quantum efficiency (EQE). MR-TADF emitters are typically fused p- and n-doped polyaromatic hydrocarbon compounds in which electron-rich donor and/or electron-deficient atoms are typically disposed *meta* to each other. This regiochemistry induces an alternating increasing and decreasing electron density distribution on adjacent atoms in the excited state, a pattern that is inverted compared to that

J. Haug, S. Bräse  
Institute of Biological and Chemical Systems - Functional Molecular Systems  
Karlsruhe Institute of Technology (KIT)  
Kaiserstrasse 12, 76131 Karlsruhe, Germany  
E-mail: [braese@kit.edu](mailto:braese@kit.edu)

J. Haug, M. Schustek, S. Bräse  
Institute of Organic Chemistry  
Karlsruhe Institute of Technology (KIT)  
Kaiserstrasse 12, 76131 Karlsruhe, Germany

J. Haug, S. Wu, M. Fatahi, E. Zysman-Colman  
Organic Semiconductor Centre, EaStCHEM School of Chemistry  
University of St Andrews  
St Andrews, Fife KY16 9ST, UK  
E-mail: [eli.zysman-colman@st-andrews.ac.uk](mailto:eli.zysman-colman@st-andrews.ac.uk)

H. Hafeez, I. D. Samuel  
Organic Semiconductor Centre, SUPA School of Physics and Astronomy  
University of St Andrews  
St Andrews, Fife KY16 9SS, UK  
E-mail: [idws@st-andrews.ac.uk](mailto:idws@st-andrews.ac.uk)

Y. T. Woordes, B. Luy  
Institute for Biological Interfaces 4 – Magnetic Resonance  
Karlsruhe Institute of Technology (KIT)  
Kaiserstrasse 12, 76131 Karlsruhe, Germany

M. Nieger  
Department of Chemistry  
University of Helsinki  
P. O. Box 55 (A. I. Virtasen aukio 1), Helsinki 00014, Finland

 The ORCID identification number(s) for the author(s) of this article can be found under <https://doi.org/10.1002/adom.202502118>

© 2025 The Author(s). Advanced Optical Materials published by Wiley-VCH GmbH. This is an open access article under the terms of the [Creative Commons Attribution](https://creativecommons.org/licenses/by/4.0/) License, which permits use, distribution and reproduction in any medium, provided the original work is properly cited.

DOI: 10.1002/adom.202502118

in the ground state. This produces low-lying excited states of short-range charge transfer (SRCT) character, leading to suitably small singlet-triplet excited-state energy gaps ( $\Delta E_{ST}$ ) to enable TADF.<sup>[2–4]</sup>

The largest family of MR-TADF emitters contains boron atoms as the electron-accepting centers and oxygen and/or nitrogen atoms as donors.<sup>[5]</sup> In 2019, Yuan et al. reported the first boron-free MR-TADF compound (**QAO**, aka **DiKTA**), substituting it for carbonyl moieties (Figure 1).<sup>[6]</sup> The OLEDs with this emitter featured a narrowband sky-blue emission ( $\lambda_{EL} = 468$  nm) and showed a maximum EQE ( $EQE_{max}$ ) of 19.4%. By decorating this core structure of bulky mesityl substituents in the design of **Mes<sub>3</sub>DiKTA** (Figure 1), we demonstrated that the aggregation-caused quenching (ACQ) inherent in the parent could be mitigated, evidenced by a higher  $EQE_{max}$  of 21.2%.<sup>[7]</sup>

Substituent regiochemistry can have an impact on the photophysics of the emitter. For instance, Li et al. investigated the effect of the regiochemistry of a phenyl substituent on the DiKTA core on the photophysical properties of the emitter, contrasting the properties of **3-PhQAD** and **7-PhQAD** (Figure 1).<sup>[8]</sup> In 2 wt% doped films in mCP, both compounds show similar photophysical properties, though the emission of **3-PhQAD** is slightly red-shifted at  $\lambda_{PL}$  of 478 nm, and there is a small increase in the photoluminescence quantum yield,  $\Phi_{PL}$ , to 73% compared to **7-PhQAD**, which emits at 472 nm and has a  $\Phi_{PL}$  of 68%. The device  $EQE_{max}$  is comparable across the OLEDs with **DiKTA**, **3-PhQAD**, and **7-PhQAD** as emitters, showing  $EQE_{max}$  of 19.4, 19.1, and 18.8%, respectively. The trend in the PL is mirrored in the electroluminescence (EL) spectra where the devices with **3-PhQAD** have the most red-shifted and broadened EL ( $\lambda_{EL}$  of 480 nm, FWHM of 44 nm [233 meV]) compared to those with **7-PhQAD** ( $\lambda_{EL}$  of 472 nm, FWHM of 34 nm [184 meV]) and **DiKTA**<sup>[6]</sup> ( $\lambda_{EL}$  of 468 nm, FWHM of 39 nm [225 meV]).

Exploring the potential of DiKTA-based emitters, we later showed that the emission could be tuned toward the red and that the orientation of the transition dipole moment (TDM) of the emitter could be induced to be strongly horizontally aligned with the substrate as a function of the number and strength of peripheral electron-donating substituents, exemplified in green and red narrowband-emitting devices with **3TPA-DiKTA** and **3DPA-DiKTA** (Figure 1), respectively, showing  $EQE_{max}$  of 30.8 and 17.9%.<sup>[9]</sup> Despite this performance, it is actually reasonably challenging to a priori design emitters whose TDM is preferentially horizontally oriented.<sup>[10]</sup> Empirically, one promising approach for enhancing the horizontal orientation of the TDM is to incorporate 9,9'-spirobifluorene (SBF) groups.<sup>[10]</sup>

Following this approach, there have been several reports of MR-TADF emitters incorporating spiro-units. Qu et al. reported two regioisomeric emitters **SF1BN** and **SF3BN** based on the **BNCz** (Figure 1) containing a SBF unit attached either at C1 or C3, respectively.<sup>[11]</sup> A significant increase in the device  $EQE_{max}$  was observed from 23.9% with **BNCz** to 35.9 and 32.2% for the


devices with **SF1BN** and **SF3BN**, respectively. These outstanding device efficiencies were attributed to the high horizontal orientation of the TDMs of 95 and 96% for **SF1BN** and **SF3BN**, respectively.

Yu et al. published a series of four emitters **SFQ**, **SOQ**, **SSQ**, and **SSeQ** (Figure 1), introducing spiro-locks into the DiKTA core.<sup>[12]</sup> The emitter **SFQ** has a near unity photoluminescence quantum yield,  $\Phi_{PL}$ , of 98.3% (3 wt% doped in mCBP), which is higher compared to the 75% reported for **DiKTA** (3.5 wt% doped in mCP). Further, the enhanced rigidity resulted in a narrowed emission reflected in the full-width at half maximum, FWHM, of 30 nm [172 meV] (3 wt% doped in mCBP; **DiKTA**: 37 nm [204 meV], 3.5 wt% doped in mCP). The incorporation of the spiro center resulted in an improved  $EQE_{max}$  of 21.7% compared to the 14.7% for the device with **DiKTA**, attributed by the authors to reduced quenching. Exploring the effect of the decoration of **SFQ** and **SOQ** with *tert*-butyl groups, Yan et al. reported a series of four emitters (**QAO-TF**, **TQAO-TF**, **TQAO-F**, and **TSOQ**, Figure 1). Modification of the DiKTA core structure with three *tert*-butyl groups resulted in a significant increase in the device  $EQE_{max}$  of 30.9, 31.7, and 30.0% for the devices with **TQAO-TF**, **TQAO-F**, and **TSOQ**, compared to 21.7% and 24.3% for the devices with **SFQ** and **SOQ**, respectively.<sup>[13]</sup> In contrast, there was only a moderate increase in the  $EQE_{max}$  of the device with **QAO-TF** ( $EQE_{max}$  of 23.3%) compared to the device with **SFQ**, where *tert*-butyl substitution is only on the spirofluorene. In 2 wt% doped films in mCBP, all four emitters showed near-unity  $\Phi_{PL}$  of 97 to 98%, similar to the 98.3 and 95.2% reported for **SFQ** and **SOQ**, respectively. Further, the 3 wt% doped films in mCBP of **TQAO-TF**, **TQAO-F**, and **TSOQ** showed narrowband emission, with FWHM of 23, 23, and 22 nm [127, 126, and 122 meV], respectively, which are narrower compared to 30 nm [172 meV] for **SFQ**, and 32 nm [185 meV] for **SOQ**. In contrast, **QAO-TF** showed broadened emission to 42 nm [235 meV]. Remarkably, the devices with **TQAO-TF**, **TQAO-F**, and **TSOQ** achieved to date some of the highest  $EQE_{max}$  among unsensitized blue OLEDs of DiKTA-based emitters. A comparative literature study of unsensitized blue OLEDs with DiKTA-based emitters, including the emitters reported in this study, is shown in Figure 2 (the data used to create the figure are summarized in Table S1, Supporting Information).


In 2025, Wu et al. reported four emitters, **SF-BN1**, **SF-BN2**, **SF-BN3**, and **SF-BN4**, consisting of two **DABNA-1**-type moieties that are fused on different fluorene fragments of the SBF.<sup>[14]</sup> **SF-BN1** and **SF-BN2** emit in the deep-blue in toluene with  $\lambda_{PL}$  of 458 and 463 nm, respectively, while **SF-BN3** and **SF-BN4** emit at  $\lambda_{PL}$  of 471 and 483 nm, respectively. All four compounds show very narrowband emission, with FWHM ranging from 15 to 21 nm [79.3 to 99.9 meV]. In 1 wt% doped films in p-PhBzCzPh, the  $\Phi_{PL}$  values exceeded 90%, with the highest value of 97.2% for **SF-BN3**. The resulting  $EQE_{max}$  increased from 22.0% for the device with device **SF-BN2** to 26.3% for the device with **SF-BN1**, reaching 29.8 and 32.2% for devices with **SF-BN3** and **SF-BN4**, respectively. These results highlight the great potential of the SBF fusion strategy.

Here, we report four narrowband sky-blue SBF-decorated DiKTA derivatives; **DiKTSBF**, **3-SBF-DiKTA**, **7-SBF-DiKTA** and **7-SBF-DiKTSBF** (Figure 1). These emitters differ in the number, regiochemistry, and point of attachment of the SBF unit. From this study, structure-property relationships become apparent, with decoration at the 7-position of **DiKTA** favoring a

O. Fuhr  
Institute of Nanotechnology (INT) and Karlsruhe Nano-Micro Facility (KNMF)  
Karlsruhe Institute of Technology (KIT)  
Kaiserstrasse 12, 76131 Karlsruhe, Germany

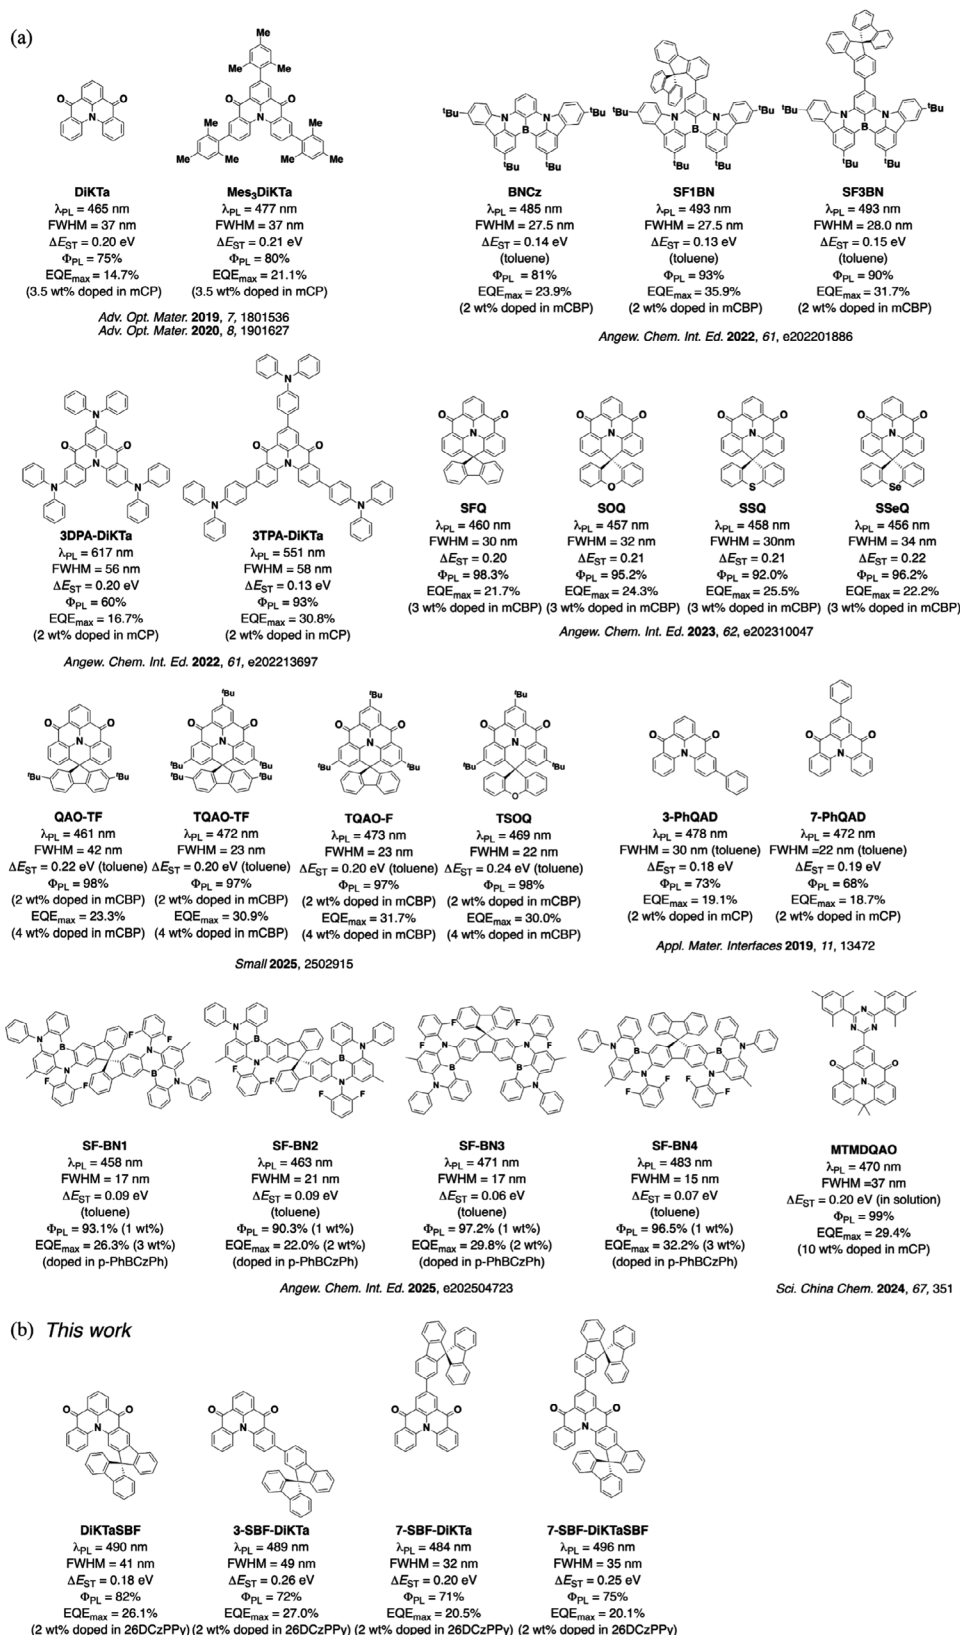

**Figure 1.** a) Literature survey of DIKTA-based and/or spiro-modified MR-TADF emitters. b) Structures and properties of emitters introduced in this study.

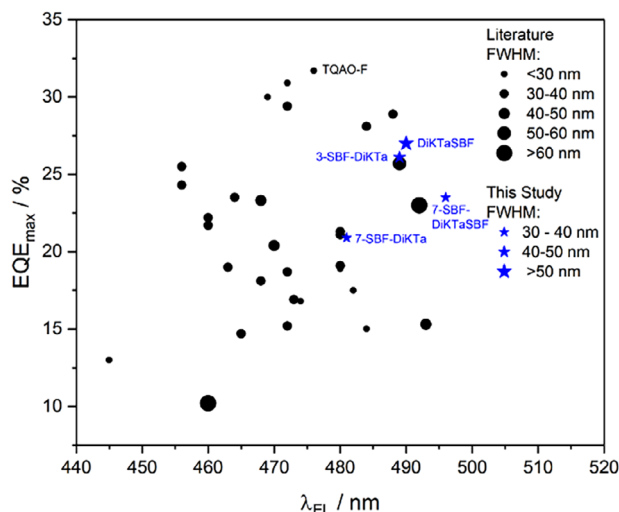

**Figure 2.** Literature survey of unsensitized blue OLEDs with DiKtA-based emitters (black circles) and the emitters reported in this study (blue stars). The size of the data point is proportional to the EL FWHM of the emitter.

narrowband emission, while substitution at the 3-position resulted in both higher  $EQE_{max}$  and reduced efficiency roll-off, resulting in device  $EQE_{max}$  of up to 27.0%. This value is among the highest  $EQE_{max}$  reported to date for unsensitized blue OLEDs with DiKtA-based emitters, highlighting the potential of spiro-decoration and carbonyl/nitrogen-based emitters.

## 2. Synthesis

The syntheses of DiKtASBF, 7-SBF-DiKtA, and 7-SBF-DiKtASBF are shown in Figure 3, and the synthesis of 3-SBF-DiKtA is shown Figure 4. In general, two synthetic routes were developed: one for accessing the SBF-fused and/or 7-position modified emitters DiKtASBF, 7-SBF-DiKtA, and 7-SBF-DiKtASBF, which are elaborated from 7-Br-DiKtA,<sup>[15]</sup> and another based on the availability of intermediate 3-I-DiKtA<sup>[16]</sup> to access 3-SBF-DiKtA.

Following the established protocol toward 7-Br-DiKtA,<sup>[15]</sup> the first step comprised the preparation of the halogenated dimethyl isophthalates (6a, 6b) in two steps via an oxidation and methylation sequence. Subsequently, these were coupled either with diphenylamine (DPA) or *N*-phenyl-9,9'-spirobi[fluoren]-2-amine (3a) using Ullmann conditions, affording 7a-7c in fair-to-good yields of 57, 72, and 80%, respectively. The intermediate 3a was prepared via a Buchwald-Hartwig amination in an excellent yield of 94%. Friedel-Craft-type ring closure reactions yielded the emitter DiKtASBF, as well as the intermediates 7-Br-DiKtA and 7-Br-DiKtASBF, in yields of 68, 42, and 19%, respectively. Optimization for the synthesis of 7-Br-DiKtASBF was attempted by varying the chlorinating agent between oxalyl chloride and thionyl chloride, as well as the Lewis acid between tin(IV) chloride and aluminum(III) chloride; however, neither strategy yielded any improvement. Incorporation of the SBF unit at the 7-position was realized via a Suzuki-Miyaura cross-coupling with (9,9'-spirobi[fluorene]-4-yl)boronic acid pinacol ester, yielding 81% of 7-SBF-DiKtA and 80% of 7-SBF-DiKtASBF.

For modification at the 3-position, 3-I-DiKtA was prepared in an overall yield of 9% according to a literature

procedure<sup>[16]</sup> in three steps consisting of a sequence of Ullmann-coupling, iodination, and Friedel-Craft-type ring closure reactions. Subsequently, the emitter 3-SBF-DiKtA was prepared via a Suzuki-Miyaura cross-coupling between 3-I-DiKtA and (9,9'-spirobi[fluoren]-4-yl)boronic acid pinacol ester (8) in an 85% yield.

The emitters were characterized by a combination of <sup>1</sup>H, <sup>13</sup>C NMR and 2D NMR spectroscopy (Figures S1–S34, Supporting Information), infrared spectroscopy (Figures S52–S68, Supporting Information), high-resolution mass spectrometry (Figures S35–S51, Supporting Information), elemental analysis (Figures S69–S71, Supporting Information), and high-performance liquid chromatography (Figures S72–S75, Supporting Information), confirming the structures and their purity.

## 3. Thermal Stability

The thermal stability was evaluated via thermogravimetric analysis (TGA) and differential scanning calorimetry (DSC) (Figure S78a, Supporting Information). All compounds are thermally stable, with 5% mass loss ( $T_d$ ) at 380, 358, 432, and 405 °C for DiKtASBF, 3-SBF-DiKtA, 7-SBF-DiKtA, and 7-SBF-DiKtASBF, respectively. Consequently, all emitters possess an enhanced thermal stability compared to DiKtA, which has a reported  $T_d$  value of 323 °C.<sup>[7]</sup> No glass transitions were observed in the DSC traces (Figure S78b, Supporting Information).

## 4. Structural Characterization

The molecular structures of DiKtASBF (Figure S76, Supporting Information) and 7-SBF-DiKtASBF (Figure S77, Supporting Information) were confirmed by single crystal X-ray diffraction studies. Crystals were grown by slow evaporation of a mixture of petroleum ether and THF. In both cases, a centrosymmetric space group is present. As a result, the unit cells of both emitters comprise both atropisomers, differing in the relative orientation at the helical pitch. Both isomers of DiKtASBF and 7-SBF-DiKtASBF are shown in Figure S79 (Supporting Information).

Significant line-broadening was observed in the <sup>1</sup>H and <sup>13</sup>C NMR spectra of all three SBF-fused compounds (DiKtASBF, 7-Br-DiKtASBF, and 7-SBF-DiKtASBF) when recorded at room temperature. Well-resolved spectra were recorded at 0 °C, allowing the assignment of the broadened resonances to the orthogonal fluorene unit of the fused SBF (Figures S85–S89, Supporting Information). This phenomenon is attributed to the conformational flexibility of the atropisomers. Temperature-dependent <sup>1</sup>H and <sup>13</sup>C NMR spectroscopy measurements (Figures S90 and S91, Supporting Information) evidence the fluctuating behavior of the emitters with increasing temperature, with the resonances at 6.6, 7.0–7.1, 7.9, and 8.3 ppm coalescing at ≈318 K. The barrier to isomerization was too high to be measured by variable temperature NMR spectroscopy.

## 5. Quantum Chemical Calculations

The frontier molecular orbitals (FMOs) were modeled using density function theory (DFT) at the PBE0/6-31G(d,p) level of theory

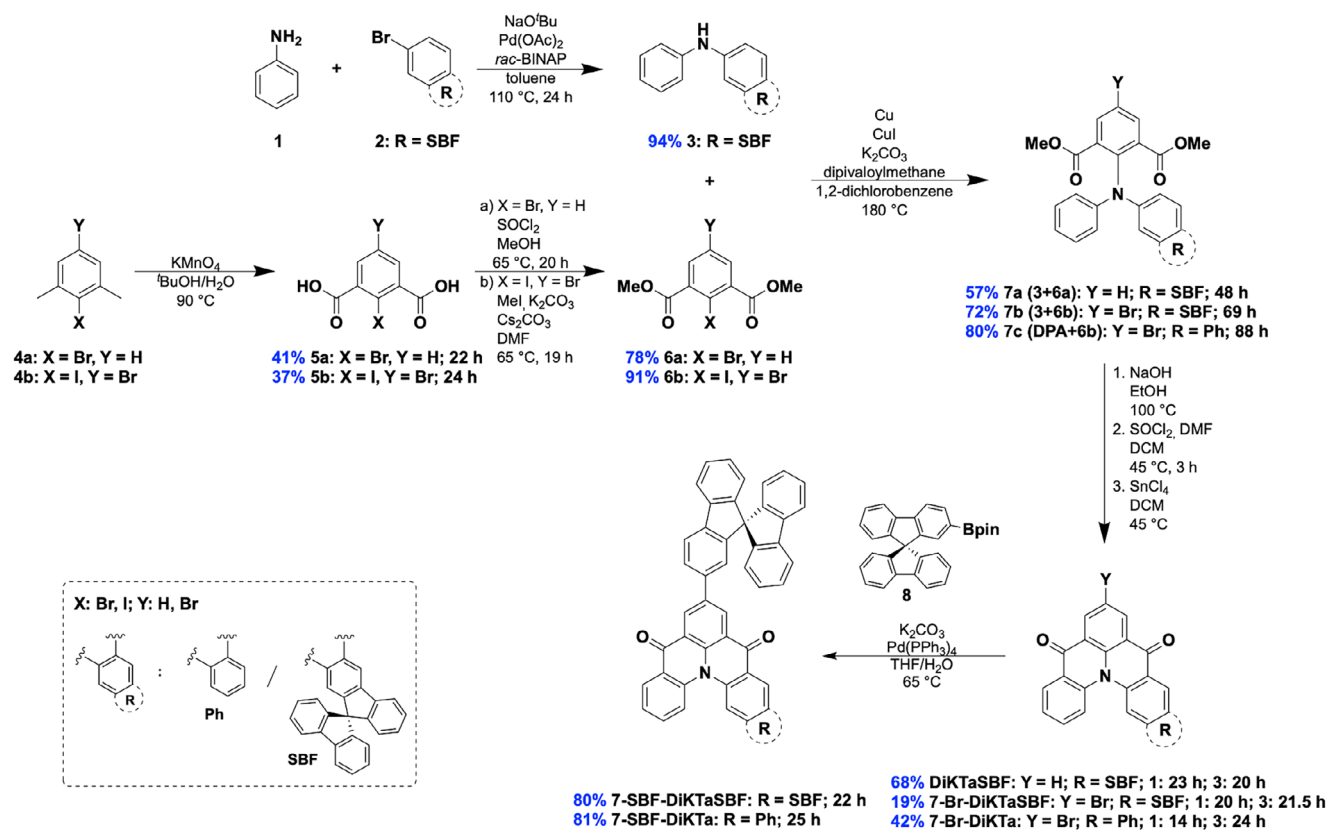


Figure 3. Synthetic route accessing DiKTaSBF, 7-SBF-DiKTa, and 7-SBF-DiKTaSBF.


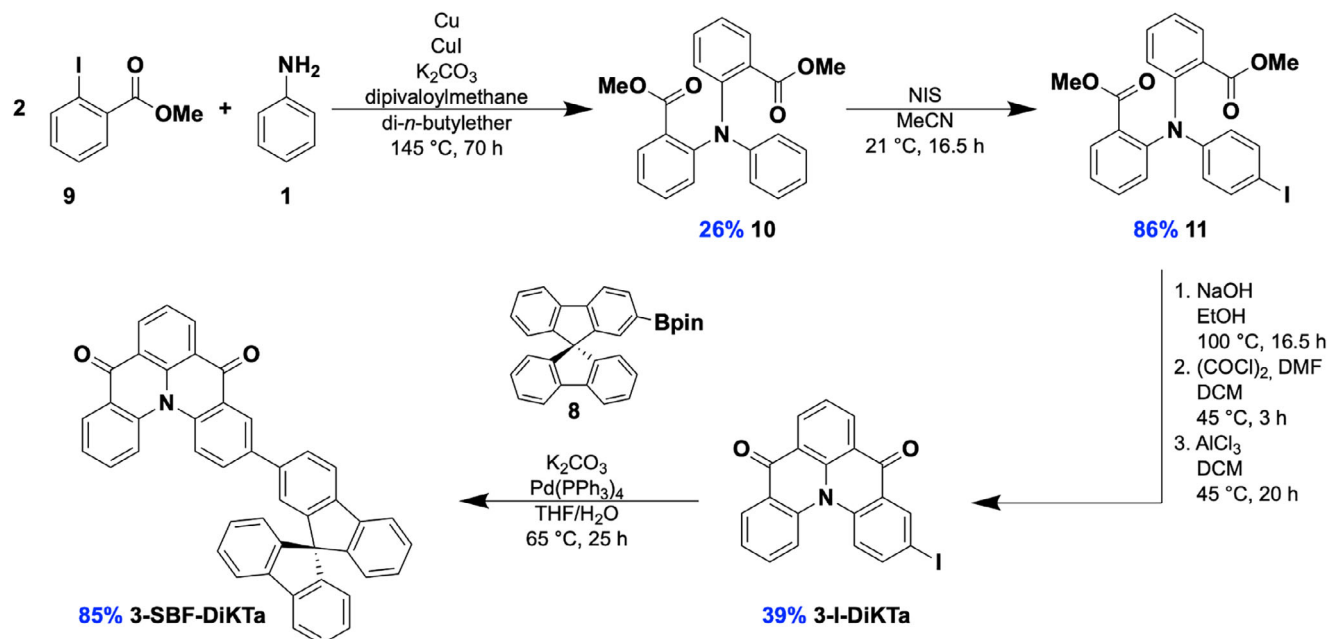


Figure 4. Synthetic route for 3-SBF-DiKTa.

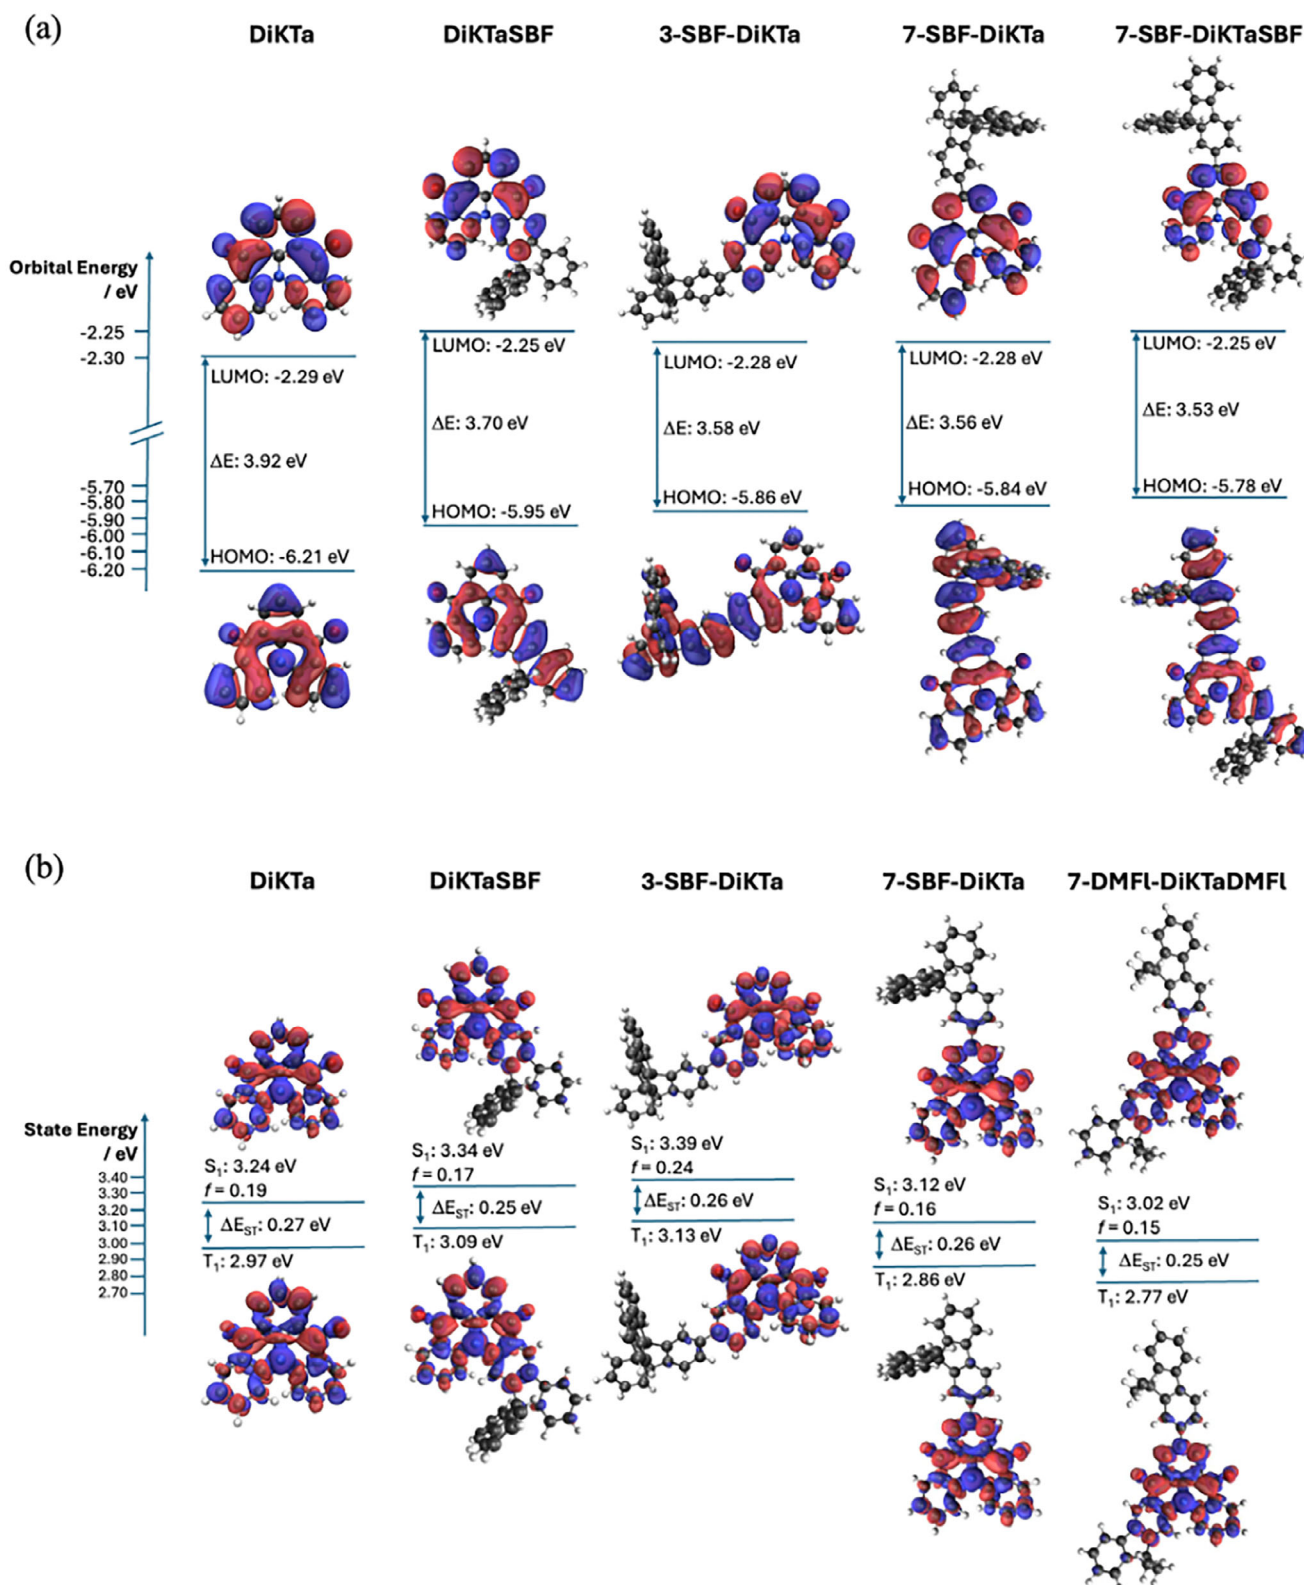

**Figure 5.** a) Calculated FMOs in toluene at the PBE0/6-31G(d,p) level of DiKTa, DiKTaSBF, 3-SBF-DiKTa, 7-SBF-DiKTa, and 7-SBF-DiKTaSBF (isovalue of 0.02); (b) Difference density plots of  $S_1$  and  $T_1$  states with the corresponding energies calculated at the SDS-ADC(2)/cc-pVDZ level for DiKTa, DiKTaSBF, 3-SBF-DiKTa, 7-SBF-DiKTa and 7-DMFL-DiKTaDMFL (isovalue of 0.001).

**Table 1.** Summary of calculated data.


|                                | HOMO/eV <sup>a)</sup> | LUMO /eV <sup>a)</sup> | $\Delta E$ /eV <sup>a)</sup> | $S_1$ /eV <sup>b)</sup> | $T_1$ /eV <sup>b)</sup> | $\Delta E_{ST}$ /eV <sup>b)</sup> | $f^{b)}$ | Linearity ratio <sup>a)</sup> | Planarity ratio <sup>a)</sup> |
|--------------------------------|-----------------------|------------------------|------------------------------|-------------------------|-------------------------|-----------------------------------|----------|-------------------------------|-------------------------------|
| DiKTa                          | -6.21                 | -2.29                  | 3.92                         | 3.24                    | 2.97                    | 0.27                              | 0.19     | 0.04                          | 0.71                          |
| DiKTaSBF                       | -5.95                 | -2.25                  | 3.70                         | 3.34                    | 3.09                    | 0.25                              | 0.17     | 0.20                          | 0.11                          |
| 3-SBF-DiKTa                    | -5.86                 | -2.28                  | 3.58                         | 3.39                    | 3.13                    | 0.26                              | 0.24     | 0.48                          | 0.12                          |
| 7-SBF-DiKTa                    | -5.84                 | -2.28                  | 3.56                         | 3.12                    | 2.86                    | 0.26                              | 0.16     | 0.45                          | 0.14                          |
| 7-SBF-DiKTaSBF                 | -5.78                 | -2.25                  | 3.53                         | –                       | –                       | –                                 | –        | 0.47                          | 0.16                          |
| 7-DMFI-DiKTaDMFI <sup>c)</sup> | -5.77                 | -2.26                  | 3.51                         | 3.02                    | 2.77                    | 0.25                              | 0.15     | 0.45                          | 0.55                          |

Calculated at the: <sup>a)</sup> PBE0/6-31G(d,p) level in toluene; <sup>b)</sup> SCS-ADC(2)/cc-pVDZ level of theory in the gas phase; <sup>c)</sup> Values based on a simplified model compound where the orthogonal fluorene units in **7-SBF-DiKTaSBF** have been replaced with *gem*-dimethyl groups.

in toluene.<sup>[17]</sup> The electron density plots of the highest occupied molecular orbital (HOMO) and lowest unoccupied molecular orbital (LUMO) are shown in **Figure 5a**, and the values are summarized in **Table 1**. The calculated HOMO energies range between -5.95 and -5.78 eV. **DiKTaSBF** has the most stabilized HOMO at -5.95 eV, followed by **3-SBF-DiKTa** and **7-SBF-DiKTa** that have nearly isoenergetic HOMOs at -5.86 and -5.84 eV, while the most destabilized HOMO of -5.78 eV is for **7-SBF-DiKTaSBF**. Compared to **DiKTa** (-6.21 eV), the HOMO is destabilized in each of these emitters, likely due to the extended conjugation into the SBF units. The HOMO density of **DiKTaSBF** only extends into the fused fluorene unit and not the orthogonal one, whereas in the coupled emitters **3-SBF-DiKTa** and **7-SBF-DiKTa**, the HOMO density extends into both fluorene units. Given the presence of two SBF units in **7-SBF-DiKTaSBF**, the most destabilized HOMO is in this compound. In contrast, nearly identical LUMO energies were computed for all the emitters, ranging narrowly from -2.25 to -2.28 eV, these are similar to the LUMO of **DiKTa** (-2.29 eV). This indicates a LUMO that is localized

about the central DiKTa core as is also evident from the plots in **Figure 5a**. Consequently, the computed HOMO-LUMO gaps range between 3.53 and 3.70 eV, which are smaller than that of **DiKTa** (3.92 eV), indicating that the absorption and emission of the emitters are likely to be red-shifted compared to those of the parent, **DiKTa**.

Given that TD-DFT calculations neglect higher-order excitations, the  $\Delta E_{ST}$  of MR-TADF emitters commonly is overestimated at this level of theory.<sup>[17]</sup> Therefore, for a more accurate modeling, computations at the RI-SCS-ADC(2)/cc-pVDZ level of theory were performed (**Figure 5b**), as double excitations are included at this level of theory. The calculated  $\Delta E_{ST}$  values are essentially the same across this family of emitters, ranging between 0.25 and 0.26 eV. These are sufficiently small and of similar magnitude to 0.27 eV for **DiKTa** (SCS-CC2/cc-pVDZ),<sup>[7]</sup> 0.26 eV for **Mes<sub>3</sub>DiKTa** (SCS-CC2/cc-pVDZ),<sup>[7]</sup> and 0.27 eV for **PCP-DiKTa** (SCS-CC2/cc-pVDZ).<sup>[18]</sup> That reverse intersystem crossing (RISC) is expected to be operational to promote TADF. Due to the increased computational demand of the larger analog **7-SBF-DiKTaSBF**, we modelled a simplified structure **7-DMFI-DiKTaDMFI** (**Figure S80**, Supporting Information), wherein the orthogonal fluorene units were replaced with geminal dimethyl groups. The energies of the first excited singlet state,  $S_1$ , of the 3-modified emitters **DiKTaSBF** (3.34 eV) and **3-SBF-DiKTa** (3.39 eV) are computed to be higher than that of **DiKTa** (3.24 eV). In contrast, the  $S_1$  states of **7-SBF-DiKTa** (3.12 eV) and **7-DMFI-DiKTaDMFI** (3.02 eV) are more stabilized. An identical trend

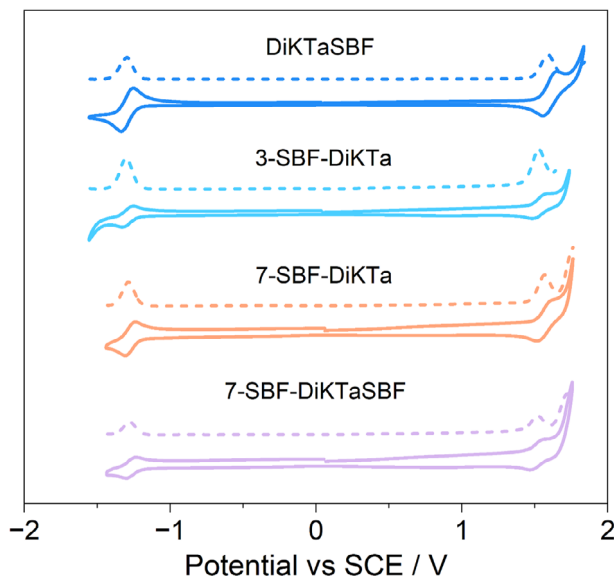

**Figure 6.** CV and DPV curves of **DiKTaSBF**, **3-SBF-DiKTa**, **7-SBF-DiKTa**, and **7-SBF-DiKTaSBF** in degassed DCM with 0.1 M [<sup>n</sup>Bu<sub>4</sub>N]PF<sub>6</sub> as the supporting electrolyte and Fc/Fc<sup>+</sup> as the internal reference. The voltammograms are referenced versus SCE (0.46 V vs SCE).<sup>[19]</sup>

**Table 2.** Summary of the electrochemistry.

|                              | $E_{ox}^{a)}$ / V versus SCE | $E_{red}^{a)}$ / V versus SCE | HOMO <sup>b)</sup> / eV | LUMO <sup>b)</sup> / eV | $\Delta E_{redox}^{c)}$ / eV |
|------------------------------|------------------------------|-------------------------------|-------------------------|-------------------------|------------------------------|
| <b>DiKTa</b> <sup>[20]</sup> | 1.78                         | -1.35                         | -6.12                   | -3.02                   | 3.10                         |
| <b>DiKTaSBF</b>              | 1.59                         | -1.30                         | -5.93                   | -3.04                   | 2.89                         |
| <b>3-SBF-DiKTa</b>           | 1.53                         | -1.30                         | -5.87                   | -3.04                   | 2.83                         |
| <b>7-SBF-DiKTa</b>           | 1.57                         | -1.29                         | -5.91                   | -3.05                   | 2.86                         |
| <b>7-SBF-DiKTaSBF</b>        | 1.52                         | -1.28                         | -5.86                   | -3.06                   | 2.80                         |

<sup>a)</sup> Measured in DCM (0.46 V for DCM/ vs SCE)<sup>[19]</sup> at a scan rate of 0.1 V/s; <sup>b)</sup> HOMO and LUMO energies were determined using  $E_{HOMO/LUMO} = -(E_{ox}/E_{red} + 4.8)$  eV, where  $E_{ox}$  and  $E_{red}$  are onset of anodic and cathodic peak potentials, respectively, calculated from DPV versus Fc/Fc<sup>+</sup>.<sup>[21]</sup> <sup>c)</sup>  $\Delta E_{redox} = |E_{HOMO} - E_{LUMO}|$ .

Table 3. Summary of the photophysical properties.

|                            | Solution  |  |   | Film   |   |  |  |                                 |  |
|----------------------------|---|--|---|--|---|--|--|---------------------------------|--|
|                            | $\lambda_{\text{PL, toluene}}$<br>(FWHM) [nm] <sup>a)</sup> | $\tau_p/\tau_d$ , toluene<br>[ns/ $\mu$ s] <sup>b)</sup> | $\Delta E_{\text{ST, 2-MeTHF}}$<br>[eV] <sup>c)</sup> | $\lambda_{\text{PL, 2 wt\%}}$ (FWHM)<br>[nm] <sup>d)</sup> | $\Phi_{\text{PL, 2wt\%}}$<br>in N <sub>2</sub> (air)<br>[%] <sup>d)</sup> | $\Phi_{\text{PL, 5 wt\%}}$ in<br>N <sub>2</sub> (air)<br>[%] <sup>d)</sup> | $\tau_p/\tau_d$<br>[ns/ $\mu$ s] <sup>e)</sup> | $S_1/T_1$<br>[eV] <sup>f)</sup> | $\Delta E_{\text{ST}}$<br>[eV] <sup>f)</sup> |
| DiKTA <sup>[9]</sup>       | 453 (27)  | 5.1 / 23   | –   | 466 (40) <sup>g)</sup>                                     | 70 (mCP)  | –  | 4.5 /<br>168 <sup>g)</sup>                     | 2.55 / 2.75 <sup>g)</sup>       | 0.20 <sup>g)</sup>                           |
| DiKTA <sup>SBF</sup>       | 476 (39)  | 6.18 / 88.7  | 0.20  | 490 (41)   | 82 (58)   | 81 (60)  | 6.96 / 394                                     | 2.47 / 2.65                     | 0.18   |
| 3-SBF-DiKTA                | 474 (35)  | 5.98 / 107   | 0.22  | 489 (49)   | 72 (54)   | 58 (44)  | 4.78 / 209                                     | 2.41 / 2.67                     | 0.26   |
| 7-SBF-DiKTA                | 470 (26)  | 5.42 / 71.5  | 0.25  | 484 (32)   | 71 (40)   | 59 (38)  | 4.52 / 1163                                    | 2.46 / 2.66                     | 0.20   |
| 7-SBF-DiKTA <sup>SBF</sup> | 485 (29)  | 6.00 / 90.5  | 0.22  | 496 (35)   | 75 (46)   | 62 (43)  | 6.63 / 632                                     | 2.39 / 2.64                     | 0.25   |

<sup>a)</sup> In dilute toluene at 300 K ( $10^{-5}$  M,  $\lambda_{\text{exc}} = 340$  nm). <sup>b)</sup> In degassed dilute toluene solution ( $10^{-5}$  M).  $\tau_p$  measured by TCSPC  $\lambda_{\text{exc}} = 375$  nm,  $\tau_d$  measured by MCS,  $\lambda_{\text{exc}} = 375$  nm. <sup>c)</sup> Determined from the onsets of the SS PL and phosphorescence spectra in 2-MeTHF at 77 K ( $\lambda_{\text{exc}} = 340$  nm). <sup>d)</sup> Spin-coated 2 and 5 wt% thin films in 26DCzPPy ( $\lambda_{\text{exc}} = 344$  nm). <sup>e)</sup> In 2 wt% 26DCzPPy film.  $\tau_p$  measured by TCSPC,  $\lambda_{\text{exc}} = 375$  nm,  $\tau_d$  measured by MCS,  $\lambda_{\text{exc}} = 344$  nm. <sup>f)</sup> Determined from the onsets of the SS-PL and phosphorescence spectra in 2 wt% 26DCzPPy films at 77 K. <sup>g)</sup> 2 wt% films in mCP, taken from the literature.<sup>[9]</sup>

was observed for the  $T_1$  energies, which are higher for DiK-Ta<sup>SBF</sup> (3.09 eV) and 3-SBF-DiKTA (3.13 eV) and lower for 7-SBF-DiKTA (2.86 eV) and 7-DMFI-DiKTA<sup>DMFI</sup> (2.77 eV) compared to DiKTA (2.97 eV). The difference density plots reveal the expected alternating pattern of increasing and decreasing electron density characteristic of MR-TADF emitters, and there are no significant differences compared to the difference density plot of DiKTA (Figure 5b). Similar to DiKTA ( $f = 0.19$ ), the  $S_0$ - $S_1$  transition for each of these compounds has a predicted oscillator strength,  $f$ , ranging between 0.15 and 0.24.

## 6. Electrochemistry

Differential pulse voltammetry (DPV) and cyclic voltammetry (CV) spectra were recorded in degassed dichloromethane (DCM) solutions with tetrabutylammonium hexafluorophosphate as the supporting electrolyte. The voltammograms are shown in Figure 6, and the data are summarized in Table 2. The data were used to infer the HOMO and LUMO energies.

All emitters showed reversible oxidation and reduction waves. Similar oxidation,  $E_{\text{ox}}$ , and reduction,  $E_{\text{red}}$ , potentials were measured for all emitters, ranging between 1.52 and 1.59 eV for  $E_{\text{ox}}$ , and  $-1.28$  and  $-1.30$  eV for  $E_{\text{red}}$ . Compared to the redox potentials of DiKTA in DCM reported in the literature,<sup>[20]</sup> all emitters possess a less positive  $E_{\text{ox}}$  (DiKTA: 1.78 V) and a similar  $E_{\text{red}}$  (DiKTA:  $-1.35$  V). The HOMO and LUMO energies in DCM range from  $-5.86$  to  $-5.93$  eV and  $-3.04$  to  $-3.06$  eV, respectively. Not surprisingly, no significant modulation of the LUMO ( $-3.02$  eV for DiKTA) was observed. However, the HOMO levels of the four emitters are destabilized compared to DiKTA ( $-6.12$  eV). These trends are in line with the computations. The resulting electrochemical gaps,  $\Delta E_{\text{redox}}$ , are thus similar among the emitters, ranging from 2.80 and 2.89 V. This implies that the incorporation type, position, and number of the SBF unit(s) does not significantly impact the HOMO and LUMO levels, but its inclusion does lead to a destabilization of the HOMO compared to DiKTA, in line with the calculations. Compared to the  $\Delta E_{\text{redox}}$  of 3.10 eV for DiKTA, all emitters thus have a smaller  $\Delta E_{\text{redox}}$ .

## 7. Photophysical Measurements

The photophysical properties of the four emitters are summarized in Table 3. Their absorption and emission spectra (Figure 7) in dilute toluene solutions ( $10^{-5}$  M) show the expected mirror image profile at room temperature and small Stokes shifts (21–28 nm) that indicate that there is only a small geometry relaxation in the excited state owing to their relatively rigid structures. The steady-state photoluminescence (SS PL) spectra reveal that these compounds emit sky-blue, with photoluminescence maxima,  $\lambda_{\text{PL}}$ , ranging from 470 nm for 7-SBF-DiKTA, 474 and 475 nm for 3-SBF-DiKTA and DiKTA<sup>SBF</sup>, to 485 nm for 7-SBF-DiKTA<sup>SBF</sup>. All compounds show narrowband emission, with FWHM of 26, 29, 35, and 39 nm (144, 151, 183, and 202 meV) for 7-SBF-DiKTA, 7-SBF-DiKTA<sup>SBF</sup>, 3-SBF-DiKTA, and DiKTA<sup>SBF</sup>, respectively. Compared to DiKTA,<sup>[20]</sup> which emits at  $\lambda_{\text{PL}}$  of 453, the emission of these derivatives is red-shifted, which is consistent with their narrower HOMO-LUMO gaps. The PL of the 7-substituted derivatives is not significantly broadened compared to DiKTA, whereas a broadening was observed for the


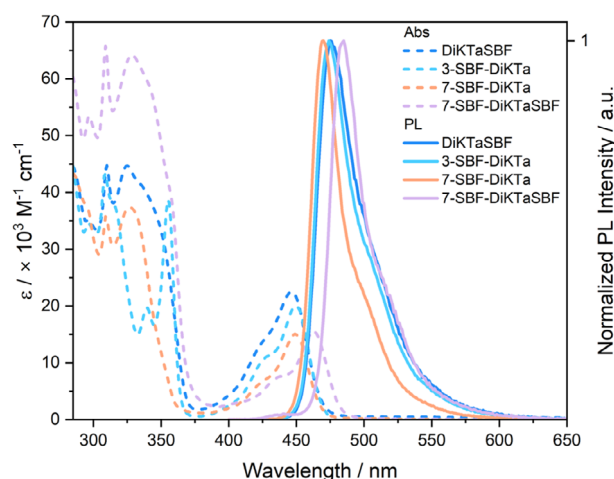


Figure 7. Absorption and photoluminescence spectra of DiKTA<sup>SBF</sup>, 3-SBF-DiKTA, 7-SBF-DiKTA, and 7-SBF-DiKTA<sup>SBF</sup> in dilute toluene ( $10^{-5}$  M,  $\lambda_{\text{exc}} = 340$  nm).

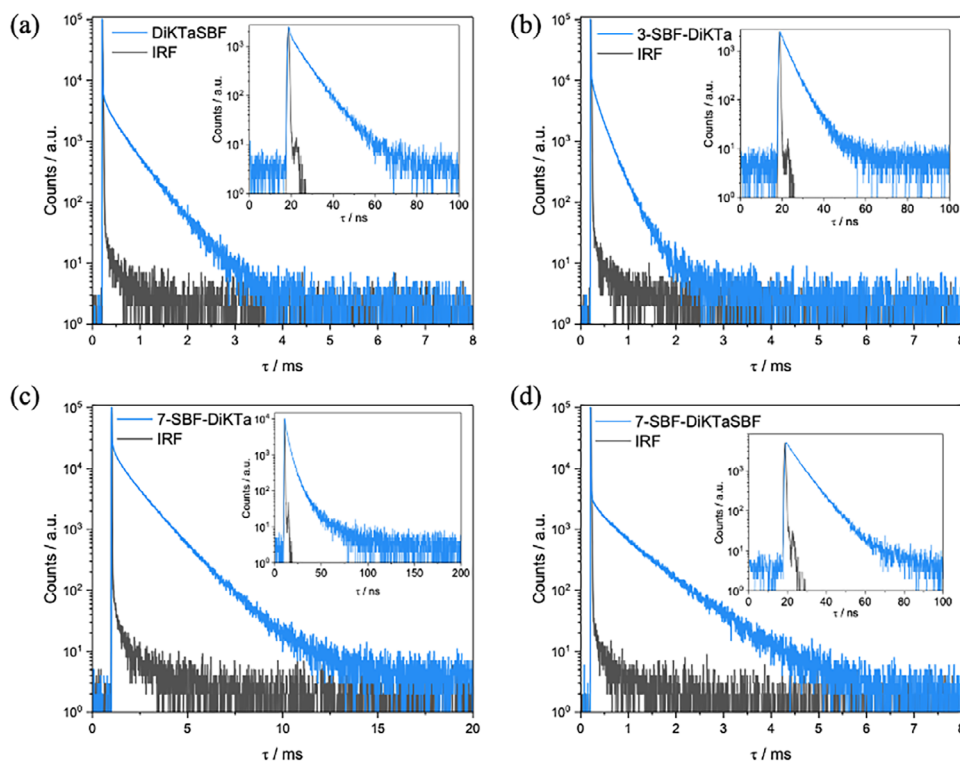

**Figure 8.** Time-resolved PL decays of the 2 wt% doped films in 26DCzPPy of a) **DiKTaSBF**, b) **3-SBF-DiKTa**, c) **7-SBF-DiKTa**, and d) **7-SBF-DiKTaSBF** with the corresponding instrument response functions (IRF). The prompt fluorescence lifetimes were measured by TCSPC ( $\lambda_{\text{exc}} = 375$  nm), whereas the delayed emission lifetimes were measured by MCS ( $\lambda_{\text{exc}} = 344$  nm).

3-substituted derivatives. All of these compounds exhibit weak positive solvatochromism (Figure S81, Supporting Information), indicating that the nature of the emissive excited state remains SRCT across these solvents.


The time-resolved PL decays in degassed toluene solution are shown in Figure S82 (Supporting Information). In toluene the PL decays with monoexponential kinetics for each of the prompt fluorescence lifetime,  $\tau_p$  and delayed fluorescence lifetime,  $\tau_d$ . All four emitters have similarly short  $\tau_p$  ranging from 5.42 to 6.18 ns, which are in line with the  $\tau_p$  of 5.1 ns reported for **DiKTa**.<sup>[20]</sup> In contrast, a more significant difference was observed for the delayed emission lifetimes  $\tau_d$ , ranging between 71.5 and 107  $\mu$ s. **7-SBF-DiKTa** features the shortest  $\tau_d$  with 71.5  $\mu$ s, followed by **DiKTaSBF** and **7-SBF-DiKTaSBF** with similar  $\tau_d$  of 88.7 and 90.5  $\mu$ s, respectively. The longest  $\tau_d$  of 107  $\mu$ s is present in **3-SBF-DiKTa**.

The  $\Delta E_{\text{ST}}$  was determined from the onsets of the steady-state PL and phosphorescence spectra at 77 K in 2-MeTHF glass (Figure S83, Supporting Information). The  $\Delta E_{\text{ST}}$  values in 2-MeTHF range narrowly between 0.20 and 0.25 eV, which align with the computed values. These values are similar to other derivatives of **DiKTa**; for instance,  $\Delta E_{\text{ST}}$  values of 0.23 eV for **SFQ** (in toluene),<sup>[12]</sup> 0.21 eV for **3DPA-DiKTa** (in 2-MeTHF),<sup>[9]</sup> and 0.16 eV for **PCP-DiKTa** (in 2-MeTHF) have been reported.<sup>[18]</sup>

To assess these emitters in OLEDs, we next measured their photophysical properties as doped films in 2,6-bis(3-(carbazol-9-yl)phenyl)pyridine (26DCzPPy).<sup>[22]</sup> This material was selected as a host due to the bipolar character, its wide band gap, and its

high triplet energy of 2.71 eV. We have employed this host in a study of a somewhat structurally related emitter, **PCP-DiKTa**, to great effect.<sup>[18]</sup> The spectra of these emitters in 2 wt% doped films in 26DCzPPy are red-shifted by about 10 to 15 nm compared to the respective ones in toluene solution, with the  $\lambda_{\text{PL}}$  in the film ranging between 484 and 496 nm (Figure S84, Supporting Information). Further, a slight broadening of the PL is observed for all emitters. As with the solution-state measurements, the PL of **7-SBF-DiKTa** and **7-SBF-DiKTaSBF** are relatively more narrowband (FWHM of 32 [166 meV] and 35 nm [173 meV], respectively), whereas the PL of **DiKTaSBF** and **3-SBF-DiKTa** are broader (FWHM of 41 [211 meV] and 49 nm [245 meV], respectively). Upon increasing the doping concentration to 5 and 10 wt%, there is a slight and progressive red-shifting observed in all cases (Figure S84, Supporting Information).

The  $\Phi_{\text{PL}}$ s of different doping ratios of emitters in 26DCzPPy films were screened, with 2 wt% doping providing the highest values for all emitters. The  $\Phi_{\text{PL}}$  values of the 2 and 5 wt% spin-coated films in 26DCzPPy are compiled in Table 3. **DiKTaSBF** has the highest  $\Phi_{\text{PL}}$  of 82% in the 2 wt% doped films, which remains at 81% in the 5 wt% doped film. The emitters **7-SBF-DiKTa**, **3-SBF-DiKTa**, and **7-SBF-DiKTaSBF** possess somewhat lower  $\Phi_{\text{PL}}$  values of 71, 72, and 75% as 2 wt% doped films, which contrastingly drop to 59, 58, and 62% upon increasing the doping ratio to 5 wt%. Therefore, 2 wt% proved to be the most promising doping concentration and was therefore selected for further photophysical investigations. Additionally, in all cases a drop in the  $\Phi_{\text{PL}}$  was observed for the aerated films to 58, 54, 40, and 46% for

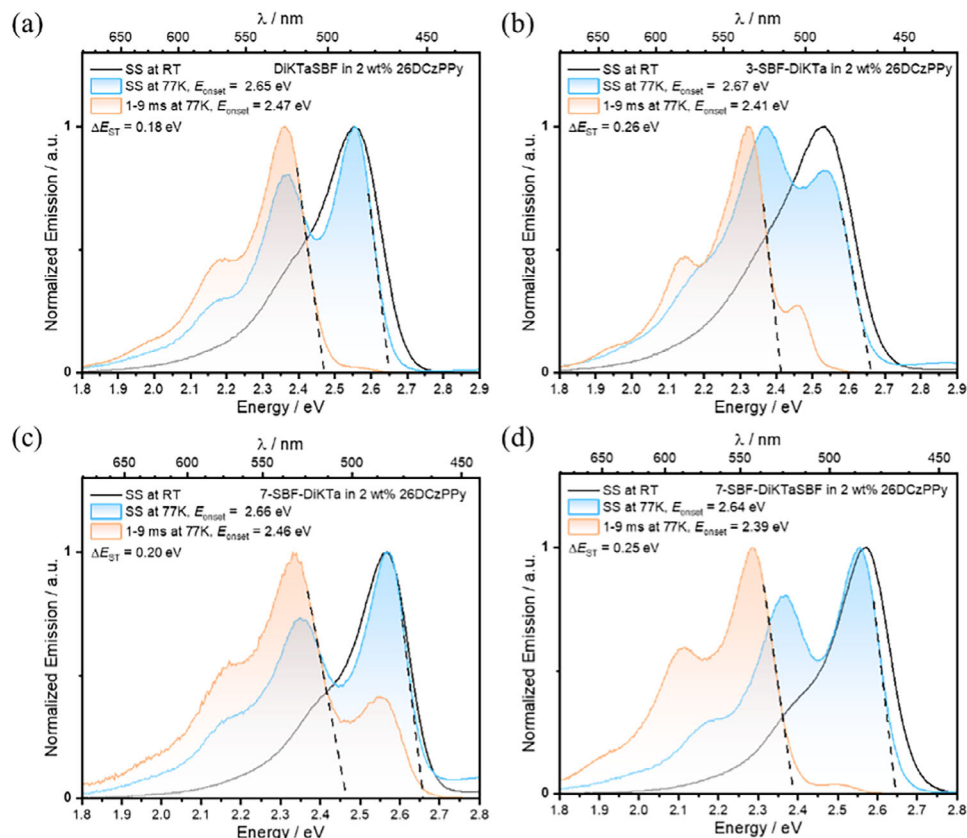

**Figure 9.** Steady-state PL and phosphorescence spectra of 2 wt% doped films of a) DiKTaSBF, b) 3-SBF-DiKTa, c) 7-SBF-DiKTa, and d) 7-SBF-DiKTaSBF at 77 K ( $\lambda_{exc} = 344$  nm) in 26DCzPPy.

DiKTaSBF, 3-SBF-DiKTa, 7-SBF-DiKTa, and 7-SBF-DiKTaSBF, respectively.

The PL of the 2 wt% doped films in 26DCzPPy decay with multiexponential kinetics, modeled as biexponential decays for both  $\tau_p$  and  $\tau_d$  (Figure 8). The average prompt lifetimes  $\tau_{p, avg}$  are similar among the four emitters and in the same range as those determined in toluene, with  $\tau_{p, avg}$  of between 4.52 and 6.89 ns. The 3-modified derivatives have significantly shorter average delayed lifetimes  $\tau_{d, avg}$  of 209 and 394  $\mu$ s for 3-SBF-DiKTa and DiKTaSBF, respectively, compared to the 7-modified derivatives, where the  $\tau_{d, avg}$  are 632 and 1,163  $\mu$ s for 7-SBF-DiKTaSBF and 7-SBF-DiKTa, respectively.


The  $\Delta E_{ST}$  was determined from the onsets of the steady-state PL and phosphorescence spectra in 2 wt% doped films in 26DCzPPy at 77 K (Figure 9). The  $\Delta E_{ST}$  values range between 0.18 and 0.26 eV. These values are of similar magnitude to those of DiKTa and many of its derivatives, such as 0.20 eV for DiKTa,<sup>[20]</sup> 0.21 eV for Mes<sub>3</sub>DiKTa,<sup>[7]</sup> and 0.23 eV for SFQ,<sup>[12]</sup> indicating that these four emitters should be TADF. This conclusion was corroborated from the temperature-dependent time-resolved PL measurements (Figure 10) of the 2 wt% doped films in 26DCzPPy, as the delayed component disappears upon cooling below 200 K, where TADF is arrested.

The excited-state kinetics were determined following the methodology of Tsuchiya et al.,<sup>[23]</sup> assuming a steady-state approximation, and compared to the values for DiKTa<sup>[24]</sup> reported

in 2 wt% doped films in mCP using literature photophysical data (Table 4). The ISC and RISC rate constants of the emitters do not exceed those of DiKTa ( $k_{ISC}$  of  $1.94 \times 10^8$  s<sup>-1</sup> and  $k_{RISC}$  of  $2.48 \times 10^4$  s<sup>-1</sup>). 7-SBF-DiKTa has a  $k_{ISC}$  of  $1.94 \times 10^8$  s<sup>-1</sup>, with  $k_{ISC}$  decreasing slightly to 1.78, 1.27, and  $1.15 \times 10^8$  s<sup>-1</sup> for 3-SBF-DiKTa, 7-SBF-DiKTaSBF, and DiKTaSBF, respectively. DiKTaSBF, 7-SBF-DiKTa, and 7-SBF-DiKTaSBF have  $k_{RISC}$  of 9.84, 4.93, and  $6.55 \times 10^3$  s<sup>-1</sup>, respectively. The  $k_{RISC}$  of 3-SBF-DiKTa is one order higher in magnitude at  $2.15 \times 10^4$  s<sup>-1</sup>. This indicates that the installation of the SBF groups at the 3-position of DiKTa leads to derivatives having faster  $k_{RISC}$ .

## 8. Organic Light-Emitting Diodes

The promising photophysical properties of the emitters encouraged the fabrication of vacuum-deposited OLEDs. The device architecture and the chemical structures of the organic layers are shown in Figure 11a,b, respectively. The OLED structure consisted of: indium tin oxide (ITO)/ 1,4,5,8,9,11-hexaazatriphenylenehexacarbonitrile (HATCN, 5 nm)/ 1,1-bis[(di-4-tolylamino)phenyl]cyclohexane (TAPC, 45 nm)/ 1,3-bis(N-carbazolyl)benzene (mCP, 5 nm)/ 26DCzPPy as host (20 nm) with DiKTaSBF, 3-SBF-DiKTa, 7-SBF-DiKTa, and 7-SBF-DiKTaSBF as emitter dopants/ 1,3,5-tris(3-pyridyl-3-phenyl)benzene (TmPyPB, 45 nm)/ lithium fluoride (LiF, 1 nm)/ aluminum (Al, 100 nm). Here, HATCN was used as the

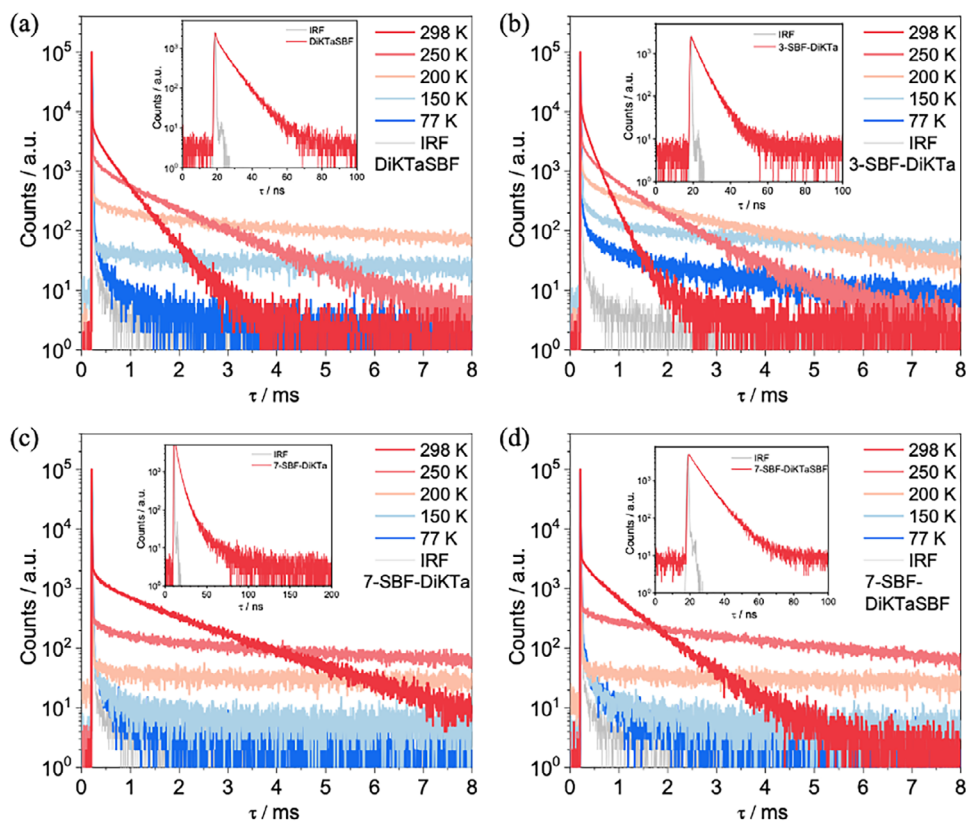

**Figure 10.** Temperature-dependent time-resolved PL measurements of the 2 wt% doped films in 26DCzPPy under vacuum ( $\lambda_{\text{exc}} = 344$  nm) of a) DiK-TaSBF, b) 3-SBF-DiKTa, c) 7-SBF-DiKTa, and d) 7-SBF-DiKTaSBF. Delayed emission lifetimes were determined by MCS ( $\lambda_{\text{exc}} = 344$  nm). Insets: the prompt PL decays at 300 K measured by TCSPC ( $\lambda_{\text{exc}} = 375$  nm).

hole injection layer, TAPC as the hole transport layer, mCP as an exciton blocking layer, TmPyPB as electron transport layer, and LiF to reduce the work function of the top Al electrode. Figure 11c shows the current density – voltage – luminance (JVL) characteristics of the 2 wt% concentration devices. The turn-on voltage of the OLEDs was between 3.8 and 4.2 V, where devices with DiKTaSBF and 3-SBF-DiKTa showed slightly higher current densities and luminance at the same voltages compared to the devices with the remaining two emitters. The external quantum efficiencies of the devices are shown in Figure 11d and Table 5. The devices with DiKTaSBF showed an  $\text{EQE}_{\text{max}}$  of 26.1%, an  $\text{EQE}_{100}$  (at  $100 \text{ cd m}^{-2}$ ) of 16.8%, and an  $\text{EQE}_{1000}$  (at  $1000 \text{ cd m}^{-2}$ ) of 6.6%. These devices emitted at  $\lambda_{\text{EL}}$  of 487 nm, which are close to the  $\lambda_{\text{PL}}$  of 490 nm of the thin film of this emitter (Table 3),


with a FWHM of 48 nm (Figure 11e). The CIE(x, y) coordinates are (0.148, 0.413), as shown in Figure 11f. The devices with 3-SBF-DiKTa showed a higher  $\text{EQE}_{\text{max}}$  of 27.0%, which dropped to an  $\text{EQE}_{100}$  of 20.0% and an  $\text{EQE}_{1000}$  of 8.8%. The devices emitted at  $\lambda_{\text{EL}}$  of 488 nm (FWHM of 52 nm) and have CIE(x, y) coordinates of (0.155, 0.421). The high  $\text{EQE}_{\text{max}}$  of devices with DiKTaSBF and 3-SBF-DiKTa are in accordance with their high  $\Phi_{\text{PL}}$  values of 82 and 72%, respectively. In addition to their high  $\Phi_{\text{PL}}$ , these emitters are preferentially horizontally oriented, with  $a$  of 72.1 and 70.6% (where 66.6% is isotropic), respectively (Figure S92, Supporting Information). This contributes to the increased light outcoupling efficiency from these OLEDs.

The OLEDs with 7-SBF-DiKTaSBF showed an  $\text{EQE}_{\text{max}}$  of 20.1%, with an efficiency drop to an  $\text{EQE}_{100}$  of 12% and an

**Table 4.** Excited-state rate constants for the films.

|                             | $\Phi_{\text{PL}}$ [%] | $\Phi_{\text{p}}$ [%] | $\Phi_{\text{d}}$ [%] | $\Phi_{\text{d}} / \Phi_{\text{PL}}$ [%] | $k_{\text{p}}$ [ $10^8 \text{ s}^{-1}$ ] | $k_{\text{d}}$ [ $10^3 \text{ s}^{-1}$ ] | $k_{\text{r}}^{\text{S}}$ [ $10^7 \text{ s}^{-1}$ ] | $k_{\text{ISC}}$ [ $10^8 \text{ s}^{-1}$ ] | $k_{\text{RISC}}$ [ $10^3 \text{ s}^{-1}$ ] |
|-----------------------------|------------------------|-----------------------|-----------------------|--|--|--|---|--|---|
| DiKTa <sup>a</sup> [24]     | 46                     | 7                     | 39                    | 85                                       | 2.08                                     | 4.1                                      | 1.42  | 1.94                                       | 24.8  |
| DiKTaSBF <sup>b</sup>       | 82                     | 20                    | 62                    | 76                                       | 1.44                                     | 2.54                                     | 2.87  | 1.15                                       | 9.84  |
| 3-SBF-DiKTa <sup>b</sup>    | 72                     | 15                    | 57                    | 79                                       | 2.09                                     | 4.78                                     | 3.12  | 1.78                                       | 21.5  |
| 7-SBF-DiKTa <sup>b</sup>    | 75                     | 12                    | 63                    | 84                                       | 2.21                                     | 0.86                                     | 2.75  | 1.94                                       | 4.93  |
| 7-SBF-DiKTaSBF <sup>b</sup> | 71                     | 16                    | 55                    | 77                                       | 1.51                                     | 1.58                                     | 2.39  | 1.27                                       | 6.55  |

<sup>a</sup>) In 1.5 wt% mCP; <sup>b</sup>) In 2 wt% 26DCzPPy. Rate constants were calculated using the steady-state approximation<sup>[23]</sup> (see Supporting Information).

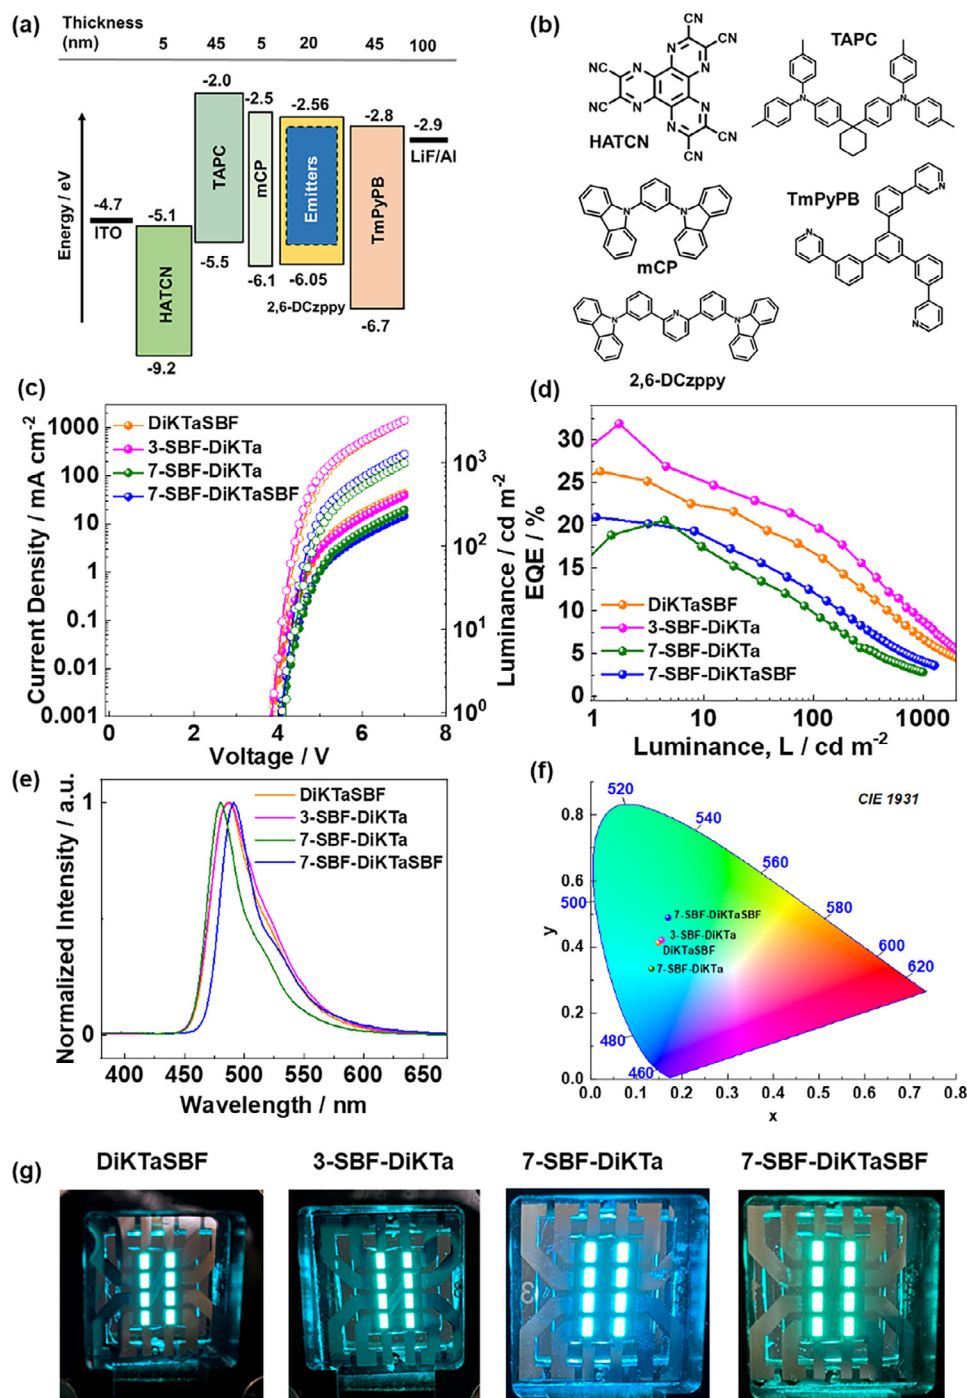

**Figure 11.** a) Schematic of the OLED stack; b) Chemical structures of the materials used in the devices; c) Current density-voltage-luminescence (JVL) characteristics with closed circles for J and open circles for L; d) External quantum efficiency (EQE) versus luminescence; e) Electroluminescence spectra; f) CIE coordinates of the devices; g) Photographs of fabricated OLEDs.

$EQE_{1000}$  of 4%. The  $\lambda_{EL}$  of the devices was at 491 nm (FWHM of 35 nm) and the CIE(x, y) coordinates were (0.169, 0.489). The devices with **7-SBF-DiKTa** also showed similar  $EQE_{max}$  of 20.5%, but the efficiency roll-off was more pronounced, with an  $EQE_{100}$  of 9.8% and an  $EQE_{1000}$  of 2.8%. The emission was slightly blue-shifted as compared to the devices with the other emitters at

$\lambda_{EL}$  of 480 nm (FWHM of 34 nm) and CIE(x, y) coordinates of (0.133, 0.334). The **7-SBF-DiKTa** and **7-SBF-DiKTaSBF** emitters have very similar  $\Phi_{PL}$  values of 71 and 75%, comparable or slightly lower than the  $\Phi_{PL}$  of the previous two emitters; however, the  $EQE_{max}$  of their OLEDs was notably lower. These emitters showed close to isotropic orientation values of 68.8 and 64.3%,

**Table 5.** Device performance for OLEDs with 2 wt% of emitter.

| Emitter        | EQE <sub>max</sub> /EQE <sub>100</sub> /EQE <sub>1000</sub> [%] | λ <sub>PL</sub> [nm] | λ <sub>EL</sub> [nm] | FWHM [nm] | CIE (x, y)   | EQE <sub>1000</sub> /EQE <sub>max</sub> [%] | FOM <sup>[25]</sup> ( $\frac{4k_f^2 k_{RISC}}{3k_f^2 + 4k_{ISC}}$ ) |
|----------------|---|----------------------|----------------------|-----------|--------------|---|---|
| DiKTaSBF       | 26.1 / 16.8 / 6.6   | 490                  | 487                  | 48        | 0.148, 0.413 | 25.3  | 1700  |
| 3-SBF-DiKTa    | 27.0 / 20.0 / 8.8   | 489                  | 488                  | 52        | 0.155, 0.421 | 32.6  | 2170  |
| 7-SBF-DiKTa    | 20.5 / 9.8 / 2.8  | 484                  | 480                  | 34        | 0.133, 0.334 | 13.7  | 555   |
| 7-SBF-DiKTaSBF | 20.1 / 12.0 / 4.0   | 496                  | 491                  | 35        | 0.169, 0.489 | 19.9  | 827   |

respectively (Figure S92, Supporting Information). Photographs of the 2 wt% OLEDs are shown in Figure 11g. The comparison of the device performances with 2 and 5 wt% emitter concentrations is shown in Figure S94 and Table S5 (Supporting Information).

We now consider the origin of the efficiency roll-off in these OLEDs. Efficiency roll-off arises from processes involving long-lived triplets and can be mitigated by reducing the triplet population. The triplet population is determined by the interplay of forward and reverse intersystem crossing together (i.e., ISC/RISC) with the radiative rate. To reduce the triplet population and hence reduce efficiency roll-off, the figure of merit (FOM)  $\frac{4k_f^2 k_{RISC}}{3k_f^2 + 4k_{ISC}}$  should be maximized.<sup>[25]</sup> We show this FOM in Table 5 and find it is highest for the device with **3-SBF-DiKTa**, slightly lower for the device with **DiKTaSBF**, substantially lower for the device with **7-SBF-DiKTaSBF** and even lower for the device with **7-SBF-DiKTa**. Accordingly, we would expect efficiency roll-off to be smallest for the device with **3-SBF-DiKTa** and highest for the device with **7-SBF-DiKTa**. We take EQE<sub>1000</sub>/EQE<sub>max</sub> as a measure of the efficiency roll-off (Table 5), where lower values of EQE<sub>1000</sub>/EQE<sub>max</sub> indicate more severe efficiency roll-off. We find that the trend in device efficiency roll-off is correlated with the trend in FOM (Figure S95, Supporting Information).

## 9. Conclusion

We have designed four novel narrowband sky-blue **DiKTa**-based SBF-modified MR-TADF emitters **DiKTaSBF**, **3-SBF-DiKTa**, **7-SBF-DiKTa** and **7-SBF-DiKTaSBF**, differing in number, position, and incorporation type of the SBF unit. Structure-property relationships were identified, and there is a significant impact of the substituent position on the photophysical properties and corresponding device performance. Substitution at the 3-position led to devices with higher efficiencies, with EQE<sub>max</sub> of up to 27.0% and alleviated efficiency roll-off. This is likely primarily due to an enhanced light outcoupling observed for the 3-position modified emitters **DiKTaSBF** and **3-SBF-DiKTa**, which reflects the increased horizontal orientation of their transition dipole moments compared to the 7-position modified emitters. The prediction of horizontal orientation remains challenging; however, trends were observed showing that more linear and planar molecules generally show preferred horizontal alignment.<sup>[10]</sup> However, this is not the case in our study. For instance, **DiKTaSBF**, with the smallest computed linearity and planarity ratio, has the most horizontally oriented TDM. Compounds **3-SBF-DiKTa**, **7-SBF-DiKTa**, and **7-SBF-DiKTaSBF** have similar linearity and planarity ratios, with the linearity ratio being much larger than that of **DiKTaSBF**. Thus, these parameters do not explain the differences in

EQE<sub>max</sub> observed between the device with **3-SBF-DiKTa**, which has a preferentially horizontally oriented TDM, and **7-SBF-DiKTa** and **7-SBF-DiKTaSBF** that are isotropically oriented. Besides the outcoupling efficiency, the EQE also depends on the internal quantum efficiency (IQE), which itself is a function of the Φ<sub>PL</sub>. Similar Φ<sub>PL</sub> values and similar fractions of the delayed fluorescence quantum yield, Φ<sub>d</sub>, to the Φ<sub>PL</sub> were observed; therefore, no significant differences in the IQE are expected. Additionally, there is no correlation between the computed oscillator strength and the observed Φ<sub>PL</sub>, indicating that the variability in Φ<sub>PL</sub> is governed by the differences in non-radiative decay rate constants.

The magnitude of the device efficiency roll-off can be understood in terms of the figure of merit (FOM) (Figure S95, Supporting Information). Higher FOM should lead to lower efficiency roll-off, and that is what we observe. **3-SBF-DiKTa** has the highest FOM and mildest efficiency roll-off. **DiKTaSBF**, **7-SBF-DiKTaSBF**, and **7-SBF-DiKTa** have progressively lower FOM, which translates to progressively larger efficiency roll-off. These trends do not correlate with the magnitude of the ΔE<sub>ST</sub>, where **3-SBF-DiKTa** has the largest gap.

Previously, Li et al. reported that phenyl substitution of **DiKTa** at the 7-position favors narrowband emission compared to substitution at the 3-position.<sup>[8]</sup> Our results are consistent with these observations, where the PL spectra of **7-SBF-DiKTa** and **7-SBF-DiKTaSBF** are relatively narrower than **DiKTa**, while those of **DiKTaSBF** and **3-SBF-DiKTa** are broader. Further, no significant impact on the optoelectronic properties was observed between fusion and coupling of the SBF unit. However, **DiKTaSBF** was less sensitive to aggregation-caused quenching of its PL, implicating that fusion of the SBF motif is a promising strategy for mitigating ACQ without adversely affecting other photophysical properties. The combination of fusion at the 3-position and substitution at the 7-position resulted in nearly identical optoelectronic behavior as the emitter having an SBF substituent solely at the 7-position.

In general, the incorporation of the SBF units within the **DiKTa** scaffold led to increased devices showing increased EQE compared to devices with **DiKTa**,<sup>[7]</sup> with modification in 3-position alleviating the roll-off and modification in 7-position resulting in narrower emission compared to **DiKTa**. Overall, these results show the significant impact of the modification site on the photophysical and optoelectronic behavior, highlighting the importance of these considerations for the design of future compounds.

## Supporting Information

Supporting Information is available from the Wiley Online Library or from the author.

## Acknowledgements

J.H. thanks the Studienstiftung des deutschen Volkes. S.W. thanks the China Scholarship Council (201906250199). The authors thank Dr. Tomas Matulaitis for help with some of the photophysical characterization. The authors acknowledge the support of Luca Schichtel for his help with the synthesis. The authors acknowledge the help of Dr. Andreas Rapp for the low-temperature <sup>1</sup>H NMR measurements. The authors thank Dr. Gavin Peters for conducting the TGA and DSC measurements. The authors acknowledge support by the state of Baden-Württemberg through bwHPC and the German Research Foundation (DFG) through grant no INST 40/575-1 FUGG (JUSTUS 2 cluster). This project has been partly funded by the European Union Horizon 2021 research and innovation programme under grant agreement No. 101073045 (TADF solutions) and the EPSRC grant EP/X026175/1. We thank the EPSRC (EP/Z535291/1, EP/W007517/1, and EP/W015137/1) for financial support.

## Conflict of Interest

The authors declare no conflict of interest.

## Author Contributions

J.H. contributed to conceptualization, data curation, formal analysis, investigation, methodology, visualization, writing – original draft, and writing – review and editing. S.W. was involved in conceptualization, data curation, formal analysis, investigation, methodology, and writing – review and editing. H.H. contributed to data curation, formal analysis, investigation, methodology, visualization, writing – original draft, and writing – review and editing. M.S. contributed to the investigation. M.F. contributed to investigation and writing – review and editing. Y.T.W. participated in data curation, investigation, methodology, and writing – review and editing. M.N. contributed to formal analysis, investigation, and writing – review and editing. O.F. contributed to formal analysis, investigation, and writing – review and editing. B.L. was involved in investigation, methodology, and supervision. I.D.W.S. contributed to conceptualization, funding acquisition, methodology, project administration, resources, supervision, and writing – review and editing. S.B. contributed to conceptualization, funding acquisition, methodology, project administration, resources, supervision, and writing – review and editing. E.Z.-C. contributed to conceptualization, funding acquisition, methodology, project administration, resources, supervision, and writing – review and editing.

## Data Availability Statement

The data that support the findings of this study are openly available in Pure at <https://doi.org/10.17630/d624631f-8adb-4a88-88e9-0e6f08a9671c>, reference number 320942690, and in the Chemotion Repository at [https://dx.doi.org/10.14272/collection/JAH\\_2023-06-01](https://dx.doi.org/10.14272/collection/JAH_2023-06-01).

## Keywords

multiresonant thermally activated delayed fluorescence, organic light-emitting diodes, spirofluorene, structure-property relationship, thermally activated delayed fluorescence

Received: July 2, 2025  
Revised: October 14, 2025  
Published online:

[1] T. Hatakeyama, K. Shiren, K. Nakajima, S. Nomura, S. Nakatsuka, K. Kinoshita, J. Ni, Y. Ono, T. Ikuta, *Adv. Mater.* **2016**, *28*, 2777.

- [2] S. Madayanad Suresh, D. Hall, D. Beljonne, Y. Olivier, E. Zysman-Colman, *Adv. Funct. Mater.* **2020**, *30*, 1908677.
- [3] J. M. Dos Santos, D. Hall, B. Basumatary, M. Bryden, D. Chen, P. Choudhary, T. Comerford, E. Crovini, A. Danos, J. De, S. Diesing, M. Fatahi, M. Griffin, A. K. Gupta, H. Hafeez, L. Hämmerling, E. Hanover, J. Haug, T. Heil, D. Karthik, S. Kumar, O. Lee, H. Li, F. Lucas, C. F. R. Mackenzie, A. Mariko, T. Matulaitis, F. Millward, Y. Olivier, Q. Qi, et al., *Chem. Rev.* **2024**, *124*, 13736.
- [4] G. Hong, X. Gan, C. Leonhardt, Z. Zhang, J. Seibert, J. M. Busch, S. Bräse, *Adv. Mater.* **2021**, *33*, 2005630.
- [5] X. Wu, S. Ni, C.-H. Wang, W. Zhu, P.-T. Chou, *Chem. Rev.* **2025**, *125*, 6685.
- [6] Y. Yuan, X. Tang, X.-Y. Du, Y. Hu, Y.-J. Yu, Z.-Q. Jiang, L.-S. Liao, S.-T. Lee, *Adv. Opt. Mater.* **2019**, *7*, 1801536.
- [7] D. Hall, S. M. Suresh, P. L. dos Santos, E. Duda, S. Bagnich, A. Pershin, P. Rajamalli, D. B. Cordes, A. M. Z. Slawin, D. Beljonne, A. Köhler, I. D. W. Samuel, Y. Olivier, E. Zysman-Colman, *Adv. Opt. Mater.* **2020**, *8*, 1901627.
- [8] X. Li, Y.-Z. Shi, K. Wang, M. Zhang, C.-J. Zheng, D.-M. Sun, G.-L. Dai, X.-C. Fan, D.-Q. Wang, W. Liu, Y.-Q. Li, J. Yu, X.-M. Ou, C. Adachi, X.-H. Zhang, *ACS Appl. Mater. Interfaces* **2019**, *11*, 13472.
- [9] S. Wu, A. Kumar Gupta, K. Yoshida, J. Gong, D. Hall, D. B. Cordes, A. M. Z. Slawin, I. D. W. Samuel, E. Zysman-Colman, *Angew. Chem., Int. Ed.* **2022**, *61*, 202213697.
- [10] F. Tenopala-Carmona, O. S. Lee, E. Crovini, A. M. Neferu, C. Murawski, Y. Olivier, E. Zysman-Colman, M. C. Gather, *Adv. Mater.* **2021**, *33*, 2100677.
- [11] Y.-K. Qu, D.-Y. Zhou, F.-C. Kong, Q. Zheng, X. Tang, Y.-H. Zhu, C.-C. Huang, Z.-Q. Feng, J. Fan, C. Adachi, L.-S. Liao, Z.-Q. Jiang, *Angew. Chem., Int. Ed.* **2022**, *61*, 202201886.
- [12] Y.-J. Yu, Z.-Q. Feng, X.-Y. Meng, L. Chen, F.-M. Liu, S.-Y. Yang, D.-Y. Zhou, L.-S. Liao, Z.-Q. Jiang, *Angew. Chem., Int. Ed.* **2023**, *62*, 202310047.
- [13] H.-Y. Yan, D.-Y. Zhou, S.-J. Ge, Y.-J. Yu, H.-T. Yuan, R.-H. Liu, Y.-J. Yang, Y. Wang, L.-S. Liao, Z.-Q. Jiang, *Small* **2025**, *21*, 2502915.
- [14] L. Wu, C. Liu, D. Liu, D. Li, W. Li, J. Zhang, X. Mu, Z. Xin, B. Liu, H. Qi, Z. Wang, D. Liu, S.-J. Su, Y. Zhou, S. Wu, Z. Ge, *Angew. Chem., Int. Ed.* **2025**, *64*, 202504723.
- [15] X. Qiu, G. Tian, C. Lin, Y. Pan, X. Ye, B. Wang, D. Ma, D. Hu, Y. Luo, Y. Ma, *Adv. Opt. Mater.* **2021**, *9*, 2001845.
- [16] D. Sun, S. M. Suresh, D. Hall, M. Zhang, C. Si, D. B. Cordes, A. M. Z. Slawin, Y. Olivier, X. Zhang, E. Zysman-Colman, *Mater. Chem. Front.* **2020**, *4*, 2018.
- [17] D. Hall, J. C. Sancho-García, A. Pershin, G. Ricci, D. Beljonne, E. Zysman-Colman, Y. Olivier, *J. Chem. Theory Comput.* **2022**, *18*, 4903.
- [18] Y. Xu, H. Hafeez, J. Seibert, S. Wu, J. S. O. Ortiz, J. Crassous, S. Bräse, I. D. Samuel, E. Zysman-Colman, *Adv. Funct. Mater.* **2024**, *2402036*.
- [19] N. G. Connelly, W. E. Geiger, *Chem. Rev.* **1996**, *96*, 877.
- [20] S. Wu, Y.-N. Hu, J. Wang, D. Sun, K. Wang, X.-H. Zhang, E. Zysman-Colman, *J. Mater. Chem. C* **2024**, *12*, 6177.
- [21] C. M. Cardona, W. Li, A. E. Kaifer, D. Stockdale, G. C. Bazan, *Adv. Mater.* **2011**, *23*, 2367.
- [22] S.-J. Su, C. Cai, J. Kido, *Chem. Mat.* **2011**, *23*, 274.
- [23] Y. Tsuchiya, S. Diesing, F. Bencheikh, Y. Wada, P. L. dos Santos, H. Kaji, E. Zysman-Colman, I. D. W. Samuel, C. Adachi, *J. Phys. Chem. A* **2021**, *125*, 8074.
- [24] S. Wu, L. Zhang, J. Wang, A. Kumar Gupta, I. D. W. Samuel, E. Zysman-Colman, *Angew. Chem., Int. Ed.* **2023**, *62*, 202305182.
- [25] S. Diesing, L. Zhang, E. Zysman-Colman, I. D. W. Samuel, *Nature* **2024**, *627*, 747.